

Sawtooth lattice multiferroic BeCr₂O₄: Noncollinear magnetic structure and multiple magnetic transitions

Mandujano, Hector Cein; Metta, Alejandro; Barišić, Neven; Zhang, Qiang; Tabiś, Wojciech; Muniraju, Naveen Kumar Chogondahalli; Nair, Harikrishnan S.

Source / Izvornik: **Physical Review Materials**, 2023, 7

Journal article, Published version

Rad u časopisu, Objavljena verzija rada (izdavačev PDF)

<https://doi.org/10.1103/PhysRevMaterials.7.024422>

Permanent link / Trajna poveznica: <https://urn.nsk.hr/urn:nbn:hr:217:774838>

Rights / Prava: [In copyright](#) / [Zaštićeno autorskim pravom](#).

Download date / Datum preuzimanja: **2025-03-14**



Repository / Repozitorij:

[Repository of the Faculty of Science - University of Zagreb](#)



Sawtooth lattice multiferroic BeCr_2O_4 : Noncollinear magnetic structure and multiple magnetic transitions

Hector Cein Mandujano ¹, Alejandro Metta ², Neven Barišić ^{3,4}, Qiang Zhang ⁵, Wojciech Tabiś ⁶,
Naveen Kumar Chogondahalli Muniraju ^{7,3,8,*} and Harikrishnan S. Nair ^{1,†}

¹Department of Physics, 500 West University Avenue, University of Texas at El Paso, El Paso, Texas 79968, USA

²Department of Chemistry, 500 West University Avenue, University of Texas at El Paso, El Paso, Texas 79968, USA

³Institute of Solid State Physics, Vienna University of Technology, Wiedner Hauptstraße 8–10, 1040 Vienna, Austria

⁴Department of Physics, Faculty of Science, University of Zagreb, Bijenička cesta 32, 10000 Zagreb, Croatia

⁵Neutron Scattering Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37830, USA

⁶AGH University of Science and Technology, Faculty of Physics and Applied Computer Science, 30-059 Krakow, Poland

⁷The Henryk Niewodniczanski Institute of Nuclear Physics, Polish Academy of Sciences,

152 Radzikowskiego Strasse, 31-342 Krakow, Poland

⁸Institute of Physics, Bijenička cesta 46, HR-10000 Zagreb, Croatia



(Received 13 December 2022; accepted 13 February 2023; published 28 February 2023; corrected 10 July 2023)

Noncollinear magnetic structures and multiple magnetic phase transitions in a sawtooth lattice antiferromagnet consisting of Cr^{3+} are experimentally identified in this work, thereby proposing the scenario of magnetism-driven ferroelectricity in a sawtooth lattice. The title compound, BeCr_2O_4 , displays three magnetic phase transitions at low temperatures—at $T_{N1} \approx 7.5$ K, at $T_{N2} \approx 25$ K, and at $T_{N3} \approx 26$ K—revealed through magnetic susceptibility, specific heat, and neutron diffraction in this work. These magnetic phase transitions are found to be influenced by externally applied magnetic fields. Isothermal magnetization curves at low temperatures below the magnetic transitions indicate the antiferromagnetic nature of BeCr_2O_4 with two spin-flop-like transitions occurring at $H_{c1} \approx 29$ kOe and $H_{c2} \approx 47$ kOe. Our high-resolution x-ray and neutron diffraction studies, performed on single crystal and powder samples, unambiguously determined the crystal structure as orthorhombic $Pbnm$. By performing the magnetic superspace group analysis of the neutron diffraction data at low temperatures, the magnetic structure in the temperature range $T_{N3,N2} < T < T_{N1}$ is determined to be the polar magnetic space group $P21nm.1'(00g)0s0s$ with a cycloidal magnetic propagation vector $\mathbf{k}_1 = (0, 0, 0.090(1))$. The magnetic structure in the newly identified phase below T_{N1} is determined as $P21/b.1'[b](00g)00s$ with the magnetic propagation vector $\mathbf{k}_2 = (0, 0, 0.908(1))$. The cycloidal spin structure determined in our work is usually associated with electric polarization, thereby making BeCr_2O_4 a promising multiferroic belonging to the sparsely populated family of sawtooth lattice antiferromagnets.

DOI: [10.1103/PhysRevMaterials.7.024422](https://doi.org/10.1103/PhysRevMaterials.7.024422)

I. INTRODUCTION

Single-phase multiferroics attract fundamental and technological interest due to the fact that they combine switchable electric and magnetic polarization [1–5], and consequently they offer the potential to cross-couple and positively impact the field of spintronics [6]. Simply by cross-coupling electric and magnetic degrees of freedom, one can efficiently control and thus manipulate magnetism by electric field or polarization current, which can provide a path to overcome bottlenecks in spintronics. One of the earliest experimental successes along these lines was the discovery of the magneto-electric (ME) effect in Cr_2O_3 in the 1960s [7,8]. Subsequently, a large pool of compounds have been identified and confirmed as multiferroics, including perovskites [9], delafossites [10], charge-order systems [11], lone-pair systems [12], hexagonal manganites [13], pyroxenes [14], rare-earth chromates [15],

and molecule-based systems [16], just to name a few. Exhaustive lists and details can be found in the review articles on multiferroics [3–5,17]. Multiferroics are classified into type I and II based on the strength of the coupling between magnetic and ferroelectric order parameters [18]. In type I multiferroics, the magnetic and ferroelectric ordering are well-separated in temperature, and hence they allow only a weak coupling between the electric and the magnetic degrees of freedom. The type II members, on the other hand, generally develop ferroelectricity concomitantly with the magnetic order, which is often established at low temperatures. Hence, the coupling between the two orders is stronger in the latter case. Since magnetic ordering precedes the development of electric polarization in type II multiferroics, a lot of attention has been devoted to understanding how various types of spin order can lead to the development of electric polarization through the breaking of inversion symmetry. Based on symmetry analyses, it was pointed out that spiral magnetic order breaks spatial inversion symmetry and generates electric polarization [19–22]. Such approaches successfully explained the appearance of ferroelectricity in several families of spinels [23], perovskites

*Corresponding author: cmnkumar@ifj.edu.pl

†Corresponding author: hnair@utep.edu

[9], and delafossites [10]. Most of these compounds have three-dimensional magnetic lattices. Low-dimensional counterparts are less explored; for example, there is only a single report of ferroelectricity induced by noncollinear spin order in sawtooth lattice compounds [24].

A sawtooth lattice of spins is low-dimensional and frustrated. It is a model lattice to study complex quantum phases, which was extensively explored in the case of spin half systems [25,26]. The sawtooth model is well described by the Hamiltonian $\mathcal{H} = \sum_i JS_i \cdot S_{i+2} + J'(S_i \cdot S_{i+1} + S_{i+1} \cdot S_{i+2}) - h \cdot S_i$, where S_i usually represents an $S = 1/2$ spin at site i , which has a neighboring site $i + 2$ in the spine of the sawtooth. J' is the interaction between the spine sites and the sawtooth tips, and h is the external magnetic field. Known as the Δ chain, delafossites, euchroite, metalorganic, and fluorites are spin systems that have been studied in the context of sawtooth chains [27–31].

After the pioneering work on chromate and olivine magnetoelectrics (i.e., Cr_2O_3 and BeCr_2O_4) in the 1960s, another olivine compound, Mn_2GeO_4 , was studied a decade ago in the context of multiferroicity [32]. Similar to BeCr_2O_4 , this compound also crystallizes in the orthorhombic $Pbnm$ space group and possesses a sawtooth lattice for the transition-metal cation. Interestingly, in Mn_2GeO_4 the spontaneous magnetization and electric polarization develop in the same crystallographic direction, below about 5.5 K [32,33]. A multi- \mathbf{Q} magnetic order with a commensurate (C) propagation vector $\mathbf{k}_C = (0, 0, 0)$ and an incommensurate (IC) propagation vector $\mathbf{k}_{IC} = (0.136, 0.211, 0)$ are identified [34]. The electric polarization in Mn_2GeO_4 is understood to originate from spiral spin order where ferromagnetic and ferroelectric domains synchronously switch. A recent work on another sawtooth magnetic lattice compound focuses on the atacamite compound $\text{Cu}_2\text{Cl}(\text{OH})_3$ [35]. Using high-magnetic-field experiments, a complex evolution of magnetization was traced out in the atacamite, and a plateaulike feature was observed at 315 kOe.

The importance of a sawtooth magnetic lattice extends beyond the quantum magnetism of the Δ chain or the multiferroicity of Mn_2GeO_4 . For example, the oxyselenite $\text{Fe}_2\text{O}(\text{SeO}_3)_2$ is reported to exhibit flatband dynamics and phonon anomalies [36]. Flatband systems with localized magnon states in high magnetic fields were studied recently due to the possibility of dissipationless magnonics [37–39]. Strongly frustrated interactions within the sawtooth chains and weak interlayer coupling have been reported in oxyarsenate $\text{Rb}_2\text{Fe}_2\text{O}(\text{AsO}_4)_2$ [40]. Olivine-type chalcogenides, Fe_2GeCh_4 ($Ch = \text{S}, \text{Se}, \text{Te}$), are computationally predicted as thermoelectrics [41], and they have been observed to reveal frustration-driven complex low-temperature magnetic phases [42].

The magnetic susceptibility of BeCr_2O_4 was first reported by Santoro *et al.* [43]. According to their report, BeCr_2O_4 had a Néel temperature of 28 K, a Curie-Weiss temperature of 13 K, and an effective magnetic moment of $3.2\mu_B$ per Cr. A four-sublattice Weiss model was proposed to explain the magnetism of BeCr_2O_4 . However, antiferromagnetic resonances at 29.5 and 47.7 kG suggestive of noncollinear spin arrangement [44] and spin-flops were later reported [45]. The spiral magnetic structure was then verified by neutron diffraction

study, which estimated the periodicity as 65 \AA [46]. The spiral arrangement of spins breaks inversion symmetry and leads to the generation of ferroelectricity, which was experimentally observed as a weak effect, without corresponding anomalies in dielectric permittivity or electrical conductivity at the Néel temperature [24]. In this work, we present a detailed magnetic and thermodynamic characterization of BeCr_2O_4 , mapping out a double-transition in magnetic susceptibility and specific heat at $T_{N3} \approx 26 \text{ K}$, at $T_{N2} \approx 25 \text{ K}$, and to a further low-temperature anomaly at $T_{N1} \approx 7.5 \text{ K}$.

Based on the results from our measurements, we have compiled the $H - T$ phase diagram of BeCr_2O_4 in magnetic fields up to 80 kOe. We have determined the magnetic structure of BeCr_2O_4 through neutron powder diffraction experiments and subsequent analysis using the magnetic superspace group approach. The magnetic structure at 2 K is an incommensurate structure with a propagation vector $(0, 0, 0.908(1))$ in a monoclinic supercell setting. The results presented here should motivate a reexamination of ferroelectric polarization and magnetization under high magnetic fields complemented with a magnetic structure determination of BeCr_2O_4 , especially using single crystals.

II. METHODS

Experimental techniques

The powder samples of BeCr_2O_4 used in the present work were prepared using the solid-state synthesis method by reacting BeO and Cr_2O_3 (4N purity, Sigma Aldrich) in stoichiometric ratios at 1400°C . The precursor oxides were mixed and ground using a mortar and pestle and heated up to five times, with intermediate grinding after each heating cycle that lasted for 24 h. The resulting powder samples were dark green in color and were characterized for quality by taking laboratory-based powder diffraction patterns using $\text{Cu K}\alpha$ x-rays of wavelength 1.54 \AA (Panalytical Empyrean). A crystal growth experiment was attempted using the method of optical floating zone. Although this did not result in the congruent melting of BeCr_2O_4 , thin whisker-shaped crystals were obtained from this attempt. Using those crystals, room-temperature single-crystal x-ray diffraction data were collected on a Bruker Quest Photon 200 diffractometer. The crystal structure data was collected, solved, and refined using the APEX3 software package [47]. High-resolution synchrotron x-ray diffraction experiments were performed on powder samples of BeCr_2O_4 at beamline 11-BM, Advanced Photon Source, Argonne National Lab. Synchrotron generated x-rays of wavelength 0.4811 \AA were used to collect diffraction patterns at 90 and 295 K. Magnetic properties of BeCr_2O_4 pellets were established using a Magnetic Property Measurement System (MPMS) SQUID magnetometer. Magnetic susceptibility and isothermal magnetization were measured in the temperature range 1.8–320 K in magnetic fields up to 90 kOe. The temperature dependence of specific heat was measured in zero and applied magnetic fields up to 40 kOe in a Physical Property Measurement System (PPMS). Neutron powder diffraction patterns were collected at the high-resolution time-of-flight diffractometer, POWGEN [48], at Spallation Neutron Source, Oak Ridge National Labora-

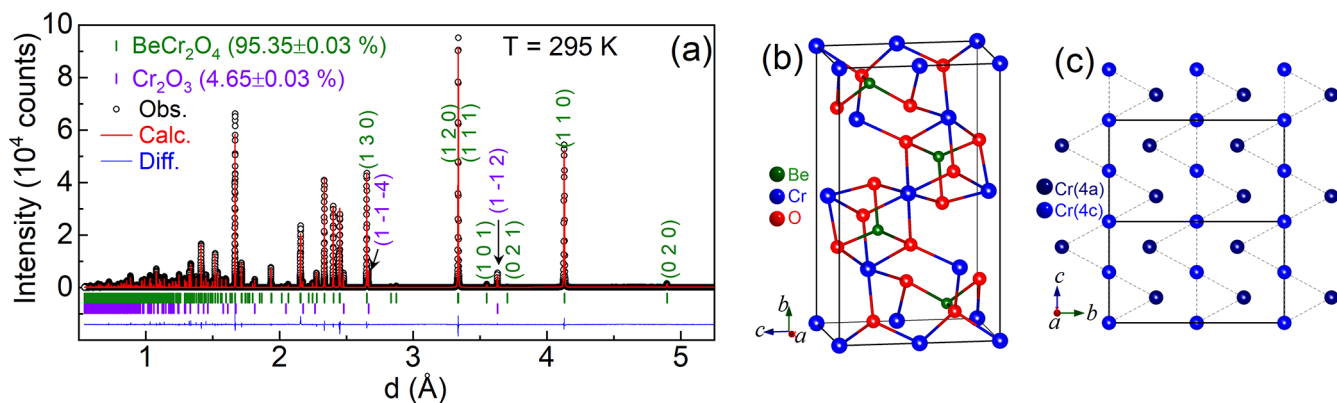


FIG. 1. (a) Synchrotron x-ray diffraction pattern of BeCr_2O_4 at 295 K along with a Rietveld fit using $Pbnm$ space group. The circles are the experimentally measured intensities, and the solid line is the calculated pattern. Top and bottom vertical bars mark the positions of the expected Bragg reflections for BeCr_2O_4 and Cr_2O_3 , respectively. The blue horizontal line at the bottom is the difference between the measured and calculated patterns. The indices of a few major reflections are indicated. (b) A clinographic view of the orthorhombic unit cell of BeCr_2O_4 . (c) The sawtooth arrangement formed by Cr atoms at $4a$ and $4c$ Wyckoff positions. The solid line indicates the unit cell boundary.

tory, at selected temperatures in the range 1.8–200 K using two data banks with center wavelengths of 1.5 and 2.665 Å. About 4 g of BeCr_2O_4 powder was loaded in a 6-mm-diam vanadium canister for those measurements. Analysis of x-ray and neutron diffraction data from 11-BM and POWGEN was performed using the FULLPROF suite of programs [49] and JANA2020 [50]. The graphical representations of lattice and magnetic structures used in this work are created using the program VESTA [51].

III. RESULTS AND DISCUSSION

A. Crystal structure

The phase-purity and the crystal structure of the powder samples of BeCr_2O_4 were checked first using the x-ray powder diffraction patterns obtained using a laboratory diffractometer. It was confirmed to crystallize in the orthorhombic space group, $Pbnm$, showing no impurity peaks. The crystal structure was further studied using high-resolution synchrotron x-ray diffraction data acquired from an 11-BM instrument at advanced photon source. The diffraction pattern at 295 K along with the Rietveld refinement is shown in Fig. 1(a). We confirmed the preliminary assignment of the orthorhombic $Pbnm$ space group [46,52] for BeCr_2O_4 through the refinement of the high-resolution synchrotron x-ray diffraction data.

BeCr_2O_4 adopts an olivine-based crystal structure similar to that of the mineral Mg_2SiO_4 . In this structure, Be^{2+} occupies a tetrahedral position, and Cr^{3+} occupies an octahedral one. An early study involving neutron diffraction had estimated the lattice parameters, $a = 4.555\text{Å}$, $b = 9.792\text{Å}$, and $c = 5.663\text{Å}$ for BeCr_2O_4 in the $Pbnm$ space group [46]. Mineral BeCr_2O_4 found in Russia was reported in the orthorhombic $P2_12_12_1$ space group, which is a subgroup of acentric $Pcmm$ [52], and also in $Pnma$ [53]. The structural parameters refined using the synchrotron x-ray diffraction data (Fig. 1) in the present work are given in Table I. The Cr atoms at the $4a$ and $4c$ Wyckoff positions form a sawtooth lattice, which is shown schematically in Fig. 1(c). This sawtooth lattice is constituted by the Cr atoms, which form isosceles

triangles with two different Cr–Cr bond distances, 2.9936(6) and 2.8367(4) Å. The bond distances and angles are listed in Table I. The edge-sharing Cr atoms are found to be about 2.83 Å apart [43]. The Cr $4a$ position has local inversion symmetry, while the $4c$ position has mirror symmetry. The four-sublattice model proposed for BeCr_2O_4 [43] takes into account the direct and superexchange pathways between Cr atoms at the inversion and mirror symmetry points. The Cr–O–Cr bond angle of 129° is more favorable to superexchange. The bond valence sums [54] determined from the analysis of the present crystal structure data indicate that the valence states of the cations in BeCr_2O_4 are $\text{Be}^{1.98}$, $\text{Cr}^{3.29}$, and $\text{Cr}^{3.03}$. We did not observe any incommensurate lattice modulations as reported by another group [55]. The unit cell obtained from the present study is similar to the mineral mariinskite [52,56] in which the Cr atoms have two independent positions and Be has only one position, both of which are in a distorted octahedral environment surrounded by oxygen atoms. The crystal structure solution using the single-crystal x-ray diffraction data confirmed the orthorhombic $Pbnm$ space group that we arrived at through powder diffraction data analysis. The results of crystal diffraction experiments are presented in Table II.

B. Magnetic properties: Multiple phase transitions

The bulk magnetic properties of BeCr_2O_4 are shown in Fig. 2. The dc magnetic susceptibility [$\chi_{\text{dc}}(T)$] was measured in the temperature range of 2–300 K under the application of different magnetic fields. A plot of the magnetic susceptibility as a function of temperature measured at 1 kOe is shown in Fig. 2(a). At high temperatures, a paramagnetic response is seen in $\chi_{\text{dc}}(T)$ which increases towards a prominent peak at around 26 K. The magnetic susceptibility further decreases beyond the peak in the low-temperature region. The inset of (a) shows the plot of the derivative $d\chi_{\text{dc}}(T)/dT$ versus temperature. Two prominent discontinuities at 25 and 26 K are recovered from the derivative of magnetic susceptibility, signifying the presence of two nearby magnetic transitions. These features were not observed in previous studies reported

TABLE I. The refined fractional atomic positions of BeCr_2O_4 obtained from the Rietveld refinement of synchrotron data (11-BM) shown in Fig. 1. The orthorhombic space group with a $Pbnm$ setting was used for the refinements. The refined lattice parameters at $T = 295$ K are $a = 4.5550(1)\text{\AA}$, $b = 9.7924(2)\text{\AA}$, and $c = 5.6651(1)\text{\AA}$. The goodness-of-fit (χ^2) was 1.85, $R_{\text{wp}} = 9.88\%$, and $R_{\text{exp}} = 5.34\%$. The bond distances and the angles are also shown. BVS stands for bond valence sums, here estimated for Be and Cr.

	x	y	z	Occupancy	$B_{\text{iso}} (\text{\AA}^2)$
Be (4c)	0.5681(1)	-0.0929(6)	0.75	1.00	0.65(4)
Cr (4a)	0.0	0.0	0.0	0.933(6)	0.13(1)
Cr (4c)	0.4974(3)	0.2311(6)	0.75	0.931(6)	0.11(4)
O1 (4c)	0.2768(6)	0.4072(3)	0.75	0.994(9)	0.40(4)
O2 (4c)	0.7289(6)	0.0612(3)	0.75	1.000(6)	0.45(3)
O3 (8d)	0.2587(3)	0.1637(3)	0.0221(3)	0.989(9)	0.48(4)
	Bond distance (\AA)		Bond angle (deg)		
	Cr(4a)-Cr(4c)	3.5021(4)	O(4c)-Cr(4a)-O(8d)	83.64(3)	
	Cr(4a)-Cr(4a)	5.3995(1)	O(4c)-Cr(4a)-O(8d)	96.37(4)	
	Cr(4a)-Cr(4a)	9.7923(2)	O(4c)-Cr(4a)-O(4c)	93.06(4)	
	Cr(4c)-Cr(4c)	3.6533(2)	Cr(4c)-O(8d)-Cr(4a)	95.78(4)	
	Cr(4c)-Cr(4c)	5.3901(2)	Cr(4c)-O(4c)-Cr(4a)	126.29(4)	
	Be(4c)-O(8d)	1.664(2)	Cr(4a)-O(4c)-Cr(4a)	92.20(5)	
	Be(4c)-O(4c)	1.571(3)	Cr(4c)-O(8d)-Cr(4c)	129.82(5)	
	BVS	Be [1.981(4)]	Cr [3.296(2)]	Cr [3.030(2)]	

on BeCr_2O_4 . The variation of low-temperature ($T < 50$ K) magnetic susceptibility with the application of different magnetic fields is shown in Fig. 2(b). The magnitude of the magnetic susceptibility is seen to increase with the application of higher values of magnetic fields. At 80 kOe, a near-saturation of low-temperature susceptibility is observed.

Figures 2(c) and 2(d) show the derivative $d\chi_{\text{dc}}/dT$ in two different temperature ranges, 4–16 and 22–28 K, respectively, at different magnetic fields. A subtle low-temperature anomaly, designated as T_{N1} , has been identified at approximately 7 K. This anomaly is not highly pronounced [panel Fig. 2(c)], but it does coincide with the more noticeable

TABLE II. The sample and crystal data as well as the details of data collection and refinements from the single-crystal structure analysis of BeCr_2O_4 .

Chemical formula	BeCr_2O_4
Formula weight (g mol^{-1})	177.01
Temperature (K)	296(2)
Wavelength (\AA)	0.71073
Crystal system	Orthorhombic
Space group	$Pbnm$
Unit-cell dimensions	$a (\text{\AA}) = 4.5576(2)$, $\alpha = 90^\circ$ $b (\text{\AA}) = 9.7970(5)$, $\beta = 90^\circ$ $c (\text{\AA}) = 5.6658(3)$, $\gamma = 90^\circ$
Volume (\AA^3)	252.98(2)
Z	4
Calculated density (g cm^{-3})	4.647
Absorption coefficient (mm^{-1})	8.370
F(000)	336
Theta range for data collection (deg)	4.16–60.01
Reflections collected	13 444
Independent reflections	2009 [$R(\text{int}) = 0.0514$]
Coverage of independent reflections	99.4%
Absorption correction	Multiscan
Structure solution program	XT, VERSION 2018/2
Refinement program	SHELXL-2019/1 (Sheldrick, 2019)
Function minimized	$\sum w(F_o^2 - F_c^2)^2$
Data/restraints/parameters	2009/0/41
Goodness-of-fit on F2	1.295
$\Delta/\sigma_{\text{max}}$	0.001
Final R indices	1758 data; $I > 2\sigma(I)$, $R1 = 0.0404$, $wR2 = 0.1041$ all data, $R1 = 0.0436$, $wR2 = 0.1084$

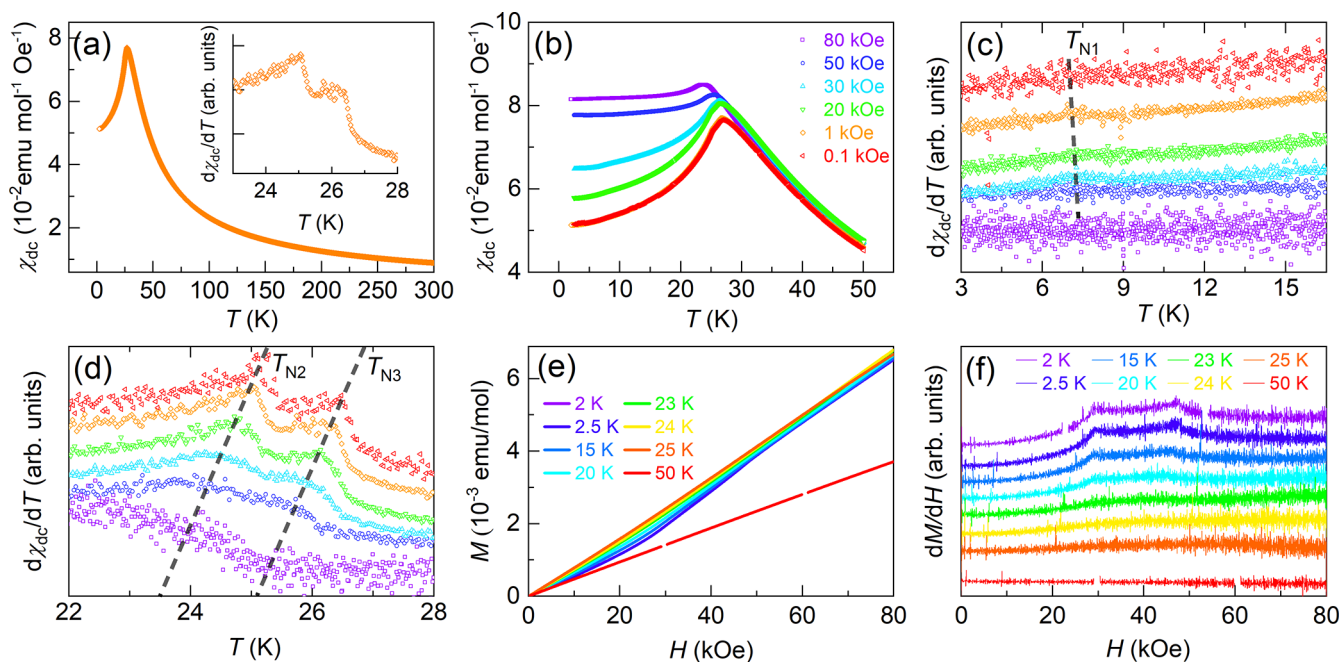


FIG. 2. (a) Magnetic susceptibility, $\chi_{dc}(T)$, of BeCr_2O_4 measured at an applied field of 1 kOe. The inset magnifies the derivative, $d\chi_{dc}(T)/dT$, in the low-temperature region, revealing a double-peak anomaly of two nearby transitions. (b) The magnetic susceptibility at different values of applied magnetic fields from 0.1 to 80 kOe. (c),(d) Derivatives $d\chi_{dc}(T)/dT$ identifying three transitions at $T_{N1} \approx 7.5$ K, $T_{N2} \approx 25$ K, and $T_{N3} \approx 26$ K. (e) The isothermal magnetization $M(H)$ at different temperatures in the range 2–50 K. (f) The derivative, dM/dH , revealing the presence of field-induced magnetic transitions.

anomaly observed in specific heat at a similar temperature. The double-peak anomalies at higher temperatures are designated T_{N2} (25 K) and T_{N3} (26 K). One of the earliest works on the magnetic susceptibility of BeCr_2O_4 reported a broad feature at approximately 28 K [46]. Although the qualitative features of the magnetic phase transition reported by Cox *et al.* are similar to the present work, our results clearly reveal three anomalies in the magnetic susceptibility of BeCr_2O_4 .

The magnetic susceptibility of BeCr_2O_4 presented in Fig. 2(a) was analyzed using the Curie-Weiss law by performing a least-squares fit to the data. An effective paramagnetic moment of $3.48(7)\mu_B/\text{Cr}$ and a Curie-Weiss temperature $\theta_{CW} = -40$ K are obtained from the fit. The paramagnetic moment value that we have obtained is comparable to, albeit slightly reduced from, the spin-only value of Cr^{3+} , $3.88\mu_B$ (d^3 , $S = 3/2$, $g \approx 2$). In comparison, the reported effective moment is $3.2\mu_B$ and $\theta_{CW} = -13$ K [43,46]. Previous study of the bulk magnetic susceptibility of BeCr_2O_4 dates back to 1963 [43]. Since a microscopic picture of the magnetic structure of Cr^{3+} was lacking at that time, a macroscopic model based on exchange interactions between the nearest-neighbor Cr atoms was put forward. As mentioned in the previous section on the crystal structure of BeCr_2O_4 , two types of Cr atoms based on the local symmetry were identified as m and i , and subsequently two interaction strengths, α and β , corresponding to $\text{Cr}_m\text{-O-Cr}_i$ and $\text{Cr}_m\text{-O-Cr}_m$, respectively, were introduced. Using these parameters, a four-sublattice model was adopted to analyze the magnetic susceptibility. It was deduced that direct magnetic exchange between Cr^{3+} moments is important in this compound. The magnetization isotherms obtained at different temperatures between 2 and 50 K are shown in Fig. 2(e) and their derivatives dM/dH in Fig. 2(f). In general,

an antiferromagnetic-like response is seen at all temperatures, except a clear change in slope is observed below 25 K down to 2 K. The derivative plot in Fig. 2(f) shows the presence of two anomalies at $H_{c1} \approx 29$ kOe and $H_{c2} \approx 47$ kOe, which can be identified as the critical fields of spin-flop-type field-induced transitions. The temperature dependence of the critical fields H_{c1} and H_{c2} is shown in Fig. 3(c).

The atacamite $\text{Cu}_2\text{Cl}(\text{OH})_3$ containing Cu sawtooth is a compound similar to BeCr_2O_4 . It enters an ordered magnetic state at 8.5 K, as seen in the magnetic susceptibility at low fields [35]. The magnetic susceptibility measured at different external magnetic fields is seen to change very little even at 13 T with the $H \parallel b$ -axis, which is identified as the easy axis. The $S = 1/2$ Cu^{2+} magnetic lattice in the atacamite results in spin-flop transitions in two different values of magnetic fields, at approximately 4 T and at 30 T when the field is applied parallel to the b -axis. These effects are also reflected in magnetostriction. Although very interesting magnetization plateaus are present in the magnetization of the atacamite, which is reminiscent of quantum effects, the current explanation for this is offered in terms of strongly coupled 1D ferromagnetic clusters that are coordinated by weak, anisotropic 2D interactions [35]. Another sawtooth magnetic lattice reported recently is that of $\text{Fe}_2\text{Se}_2\text{O}_7$ [57]. Different from the Cu sawtooth of the atacamite, the Fe sawtooth in this case orders magnetically at high temperatures, the transition temperature being at 112 K. The easy axis, in this case too, is the b -axis of an orthorhombic unit cell. Spin-flop magnetic transitions are found to occur at 5.45 T when the field is applied parallel to the b -axis. The spin chain system $\text{Rb}_2\text{Mn}_3(\text{MoO}_4)_3(\text{OH})_2$, similar to BeCr_2O_4 , shows two nearby magnetic anomalies in magnetic suscep-

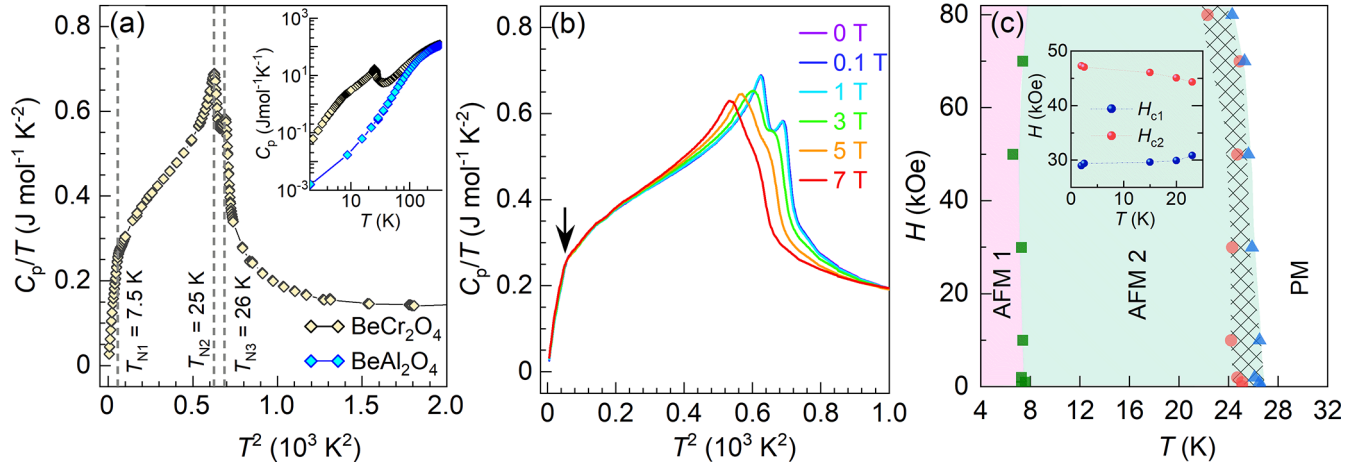


FIG. 3. (a) The low-temperature specific heat of BeCr_2O_4 plotted as C_p/T vs T^2 . Three phase transitions at $T_{N1} \approx 7.5$ K, $T_{N2} \approx 25$ K, and $T_{N3} \approx 26$ K are present, indicated by dashed vertical lines. The inset shows the total specific heat of BeCr_2O_4 and BeAl_2O_4 in the range 2–300 K in logarithmic scales. (b) The specific heat of BeCr_2O_4 under the application of different magnetic fields. T_{N2} and T_{N3} are suppressed by the fields, while T_{N1} (indicated by an arrow) is field-independent. (c) The $H - T$ phase diagram of BeCr_2O_4 constructed from the phase-transition points extracted from the specific heat and magnetic susceptibility. The inset shows the critical fields H_{c1} and H_{c2} identified in the derivatives of magnetization isotherms.

tibility and specific heat [58]. Magnetic susceptibility of this compound revealed anomalies at 4.7 and 3.2 K, while a further low-temperature kink was seen in specific heat at 2.6 K indicating a possible change of magnetic structure. A significantly high degree of frustration was seen in the compound with $f = 24$. $\text{Fe}_2\text{O}(\text{SeO}_3)_2$ is another sawtooth lattice system with a relatively high-temperature transition at 120 K [36]. A single-phase transition peak is observed with low-temperature susceptibility nearly saturating, indicating antiferromagnetic correlations being present. A spin-flop transition, common to the sawtooth systems, is indicated to be present at low applied fields, and, similar to the atacamite, ferromagnetic correlations are also speculated to be present. Hence we see a gradual trend, with some exceptions, of increasing phase-transition temperature with increasing value of spin as we look at sawtooth systems made up of Cu, Cr, Mn, and Fe spins. Common to all these systems is the presence of spin-flop magnetization transitions and plateaus at high fields.

C. Specific heat and the H - T phase diagram

The specific heat $C_p(T)$ of BeCr_2O_4 presented in Fig. 3(a) shows three prominent phase transitions at 7.5, 25, and 26 K thereby confirming the magnetic phase transitions at T_{N1} , T_{N2} , and T_{N3} previously seen in the magnetic susceptibility of the compound. The plot of $C_p(T)$ versus T^2 shown in Fig. 3(a) highlights the anomalies at T_{N1} , T_{N2} , and T_{N3} , which are more pronounced peaks than in the magnetic susceptibility curves, Fig. 2(a). The curves of total specific heat of BeCr_2O_4 and that of the nonmagnetic analogous compound BeAl_2O_4 , measured in the range 2–320 K, are shown in the inset of Fig. 3(a), plotted as $C_p(T)$ versus T , in logarithmic axes. The $C_p(T)$ of BeAl_2O_4 was used as the phonon analog to be subtracted from that of BeCr_2O_4 in order to obtain the magnetic entropy of Cr^{3+} moments as $9 \text{ J mol}^{-1} \text{ K}^{-1}$ at 27 K. Assuming $S = 3/2$ for Cr^{3+} , the

spin-only contribution to magnetic entropy can be estimated using the expression $2R \ln(2S + 1) = 23 \text{ J mol}^{-1} \text{ K}^{-1}$. A curve fit according to the Debye model to the full temperature range of total specific heat of BeAl_2O_4 resulted in the estimation of the Debye temperature θ_D (BeAl_2O_4) = 992.01(1) K. The reported Debye temperatures of BeAl_2O_4 and BeO are 1096 and 1280 K, respectively [23,59]. The Debye temperature we obtained is close to the value obtained by analyzing the low-temperature specific heat of BeAl_2O_4 using the expression $C_{\text{low}} = \alpha T + \beta T^3 + \gamma T^5$, where α , β , and γ are fitting parameters. The temperature range 2–100 K was used for the low-temperature fit, and a value of $\beta = 1.63 \times 10^{-5} \text{ J mol}^{-1} \text{ K}^{-4}$ was obtained. The Debye temperature was estimated using the expression $\theta_D = (\frac{12\pi^4 R}{5\beta}) = 941.13(2) \text{ K}$, where p is the number of atoms in the formula unit and R is the universal gas constant. Due to the presence of multiple low-temperature anomalies in BeCr_2O_4 , an analysis of specific heat using the T^3 -law was not feasible. We applied the molecular mass correction for the Debye temperature following $[MV^{2/3}\theta_D^2](\text{BeAl}_2\text{O}_4) = [MV^{2/3}\theta_D^2](\text{BeCr}_2\text{O}_4)$, where V is the unit-cell volume, to obtain θ_D (BeCr_2O_4) = 770 K. The total specific heat of BeCr_2O_4 was fitted with the Debye model [60] for phonon-specific heat, which leads to a Debye temperature θ_D (BeCr_2O_4) = 847 K.

The phase transitions at T_{N1} , T_{N2} undergo appreciable changes with the application of external magnetic fields to a value up to 70 kOe. It can be seen from Fig. 3(b) that a magnetic field of 50 or 70 kOe smoothed the twin peak near T_{N2} and T_{N3} , but they are shifted towards low temperatures very slightly. The signature of T_{N1} is indicated by the arrow in the figure where a change of slope is visible. A magnetic-field temperature (HT) phase diagram of BeCr_2O_4 , presented as Fig. 3(c), was constructed from the phase-transition points obtained from the derivatives of magnetic susceptibility and specific-heat curve. The phase diagram and the magnetic properties deduced from the bulk physical properties measure-

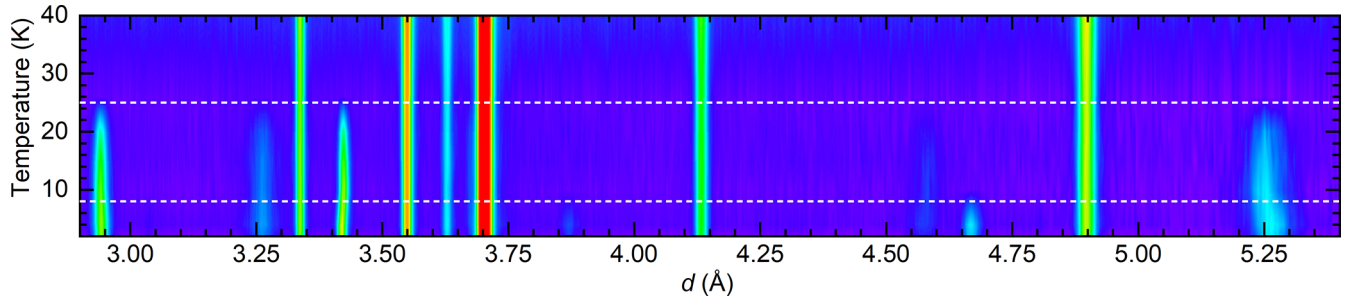


FIG. 4. A color map of temperature evolution of diffraction patterns of BeCr_2O_4 as a function of d -spacing. Magnetic phase transitions, at approximately $T_{N2,N3}$ (top horizontal dashed line) and T_{N1} (bottom horizontal line), are discernible with the appearance of additional Bragg reflections.

ments can be summarized as follows. At temperatures above ≈ 30 K, BeCr_2O_4 is paramagnetic. When the temperature is reduced below 30 K, three magnetic transitions are observed with peaks at temperatures T_{N3} , T_{N2} , and T_{N1} ($T_{N3} > T_{N2} > T_{N1}$). The double-peak high-temperature transitions (T_{N3} and T_{N2}) occur within 1 K, and the magnetic state below these transitions is designated in our HT phase diagram as AFM 2. Further, below T_{N1} , we propose another antiferromagnetic phase AFM 1. The microscopic nature of the magnetic order in the narrow temperature region between T_{N3} and T_{N2} and below T_{N1} has yet to be determined. In the subsequent sections, we will show results from neutron diffraction experiments to probe the magnetic structures of AFM 1 and AFM 2.

D. Neutron diffraction: Noncollinear magnetic structure

Based on the results of our magnetization and specific-heat measurements presented in the previous sections, three magnetic phase transitions are identified in BeCr_2O_4 at T_{N1} , T_{N2} , and T_{N3} . To elucidate the microscopic lattice and magnetic ordering at different temperatures, we performed neutron powder diffraction experiments in the range 2–295 K. The combined diffraction data obtained at several temperatures are presented in Fig. 4 in the form of a color map of the diffracted intensity, plotted as a function of temperature and d -spacing in the range 2.9–5.4 Å. Distinct transitions are discernible with the appearance of new Bragg reflections at ~ 26 and ~ 7 K. Two horizontal dashed lines are marked in Fig. 4 to indicate the temperatures below which additional Bragg reflections are observed. The top line (marked as $T_{N2,N3}$) is close to the transitions T_{N3} and T_{N2} , while the bottom line corresponds to the transition at T_{N1} . Due to the lack of finer temperature steps in the current neutron data, the magnetic ordering in the temperature range $T_{N3} > T > T_{N2}$ [the hashed region in Fig. 3(c)] could not be resolved from our neutron powder diffraction measurements, so the phase transition around this temperature region is indicated as $T_{N2,N3}$ in the following section.

The neutron diffraction pattern collected at $T = 295$ K was refined using the orthorhombic structure model (space group $Pbnm$) obtained from our x-ray diffraction data analysis. The lattice parameters obtained from the refinements are $a = 9.840(1)\text{Å}$, $b = 5.693(7)\text{Å}$, and $c = 4.577(4)\text{Å}$. These values are slightly different from the unit-cell parameters determined using synchrotron x-ray diffraction experiments

presented earlier, but they are in general agreement with the earlier reports [46]. The refined fractional coordinates at 295 K are comparable to the values obtained from the refinement of the synchrotron x-ray data given in Table I.

In Figs. 5(a)–5(c) we present the neutron powder diffraction patterns of BeCr_2O_4 collected at three exemplary temperatures, 30 K (paramagnetic), 10 K ($T_{N1} < T < T_{N2,N3}$), and 2 K ($T < T_{N1}$), along with the Rietveld refinement results of nuclear and magnetic structures. At 30 K, which is slightly above T_{N3} , the diffraction pattern shows purely nuclear contributions, as can be seen from Fig. 5(a). At 10 and 2 K, the strong magnetic Bragg peak at $d = 10\text{Å}$ is a conspicuous feature in the diffractograms; see Figs. 5(b) and 5(c). The low-temperature diffraction data below $T_{N2,N3}$ were refined using the magnetic superspace group approach [61]. Starting with the parent crystal structure ($Pbnm$), the magnetic modulation is found to be incommensurate with a modulation vector $\mathbf{k}_1 = (0, 0, 0.090(1))$ in the temperature range $T_{N1} < T_{N2,N3}$. At 2 K, in addition to the aforementioned reflections, a new set of reflections appear that can be indexed with a modulation vector $(0.5, 0.5, 0.0)$ with the parent setting. The magnetic structure below T_{N1} was refined using a superspace group approach by using a larger monoclinic supercell (Table III). With this approach, all the magnetic reflections could be indexed with a single modulation vector $\mathbf{k}_2 = (0, 0, 0.908(1))$. The best fits to the experimental data were obtained with the magnetic superspace groups $P21nm.1'(00g)0s0s$ at 10 K and $P21/a.1'[a](00g)00s$ at 2 K. The modulated unit-cell parameters are given in Table III. The resulting magnetic supercell is pictorially represented in Figs. 5(d) and 5(e) as projections along the ac plane at 10 and 2 K, respectively. The Cr^{3+} spins form a cycloid with the periodicity extending to about 65Å .

IV. DISCUSSION

Several types of magnetic ordering can lead to the development of ferroelectric polarization in type II multiferroics [62,63]. Cycloidal, conical, screw, collinear antiferromagnetic, and weak ferromagnetic order are all known to result in nonzero electric polarization. TbMnO_3 , DyMnO_3 , MnWO_4 , CuO [9,64–66], CoCr_2O_4 , ZnCr_2Se_4 [67,68], CuFeO_2 , CuCrO_2 [69,70], DyMn_2O_5 [71], DyFeO_3 , and GdFeO_3 [72,73] are examples of compounds that display the different types of magnetic order mentioned above and consequently develop electric polarization, either spontaneously

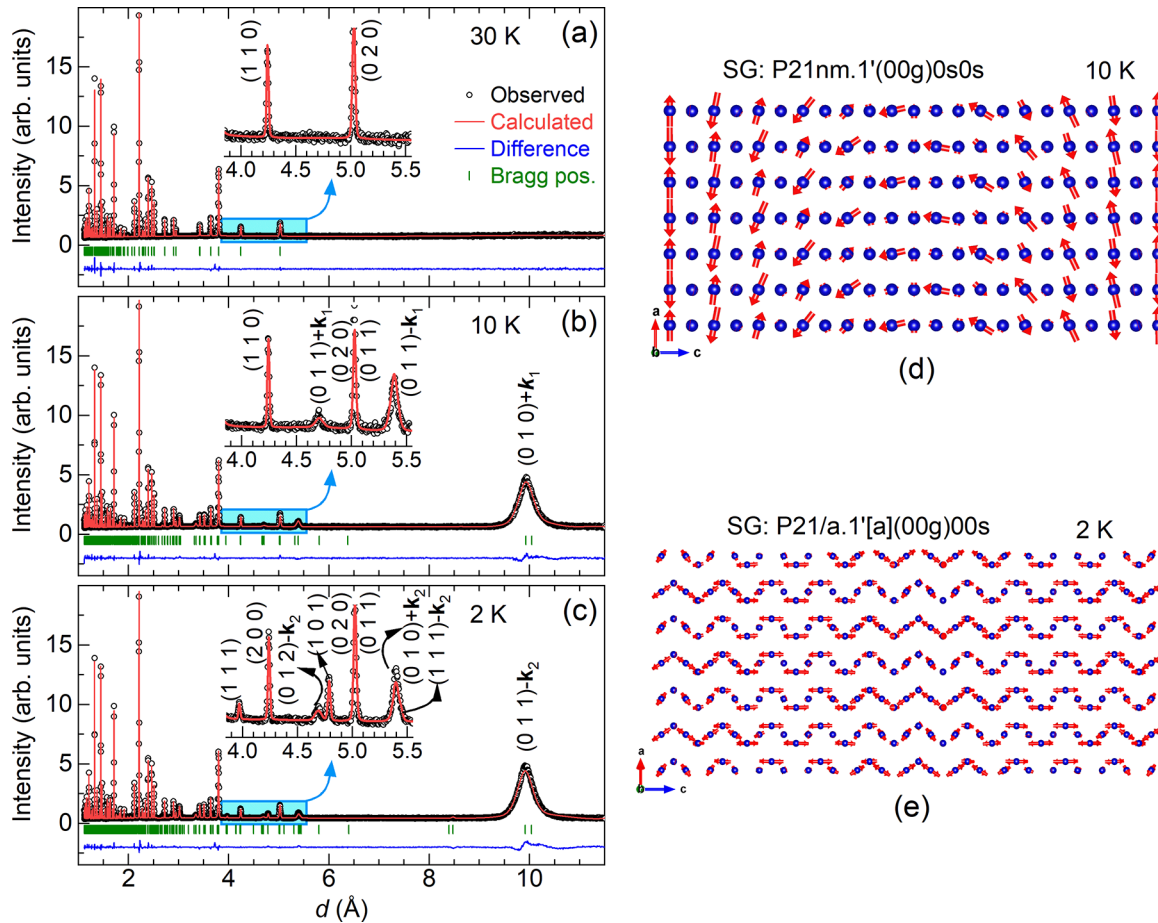


FIG. 5. Time-of-flight neutron diffraction data of BeCr_2O_4 at three different temperatures are shown along with Rietveld refinement results at (a) 30 K ($T > T_{N3}$), (b) 10 K ($T_{N1} < T < T_{N2,N3}$), and (c) 2 K ($T < T_{N1}$). Best fits to the experimental data were obtained for the superspace group $P21nm.1'(00g)0s0s$ at 10 K and $P21/b.1'[b](00g)00s$ at 2 K. The insets show a section of diffraction pattern where few additional Bragg peaks are observed compared to the 30 K data. Arrangement of Cr^{3+} spins viewed along the b direction at (d) 10 K and (e) 2 K.

or with the application of an external magnetic field. When the spins in a crystal lattice form a cycloidal modulation along a crystallographic direction, a macroscopic polarization, $P = a \sum e_{ij} \times (S_i \times S_j)$, is generated, where a is determined by spin-orbit coupling, exchange, and spin-lattice interactions, and e_{ij} is the unit vector connecting the neighboring spins S_i and S_j . This type of polarization can be explained using the spin-current model or the Katsura-Nagaosa-Balatsky model [20], which is derived from an inverse Dzyaloshinskii-Moriya model [21].

Perovskite manganites were the first to be studied from the perspective of cycloidal spin order. For example, in TbMnO_3 the Mn^{3+} spins undergo a collinear sinusoidal antiferromagnetic order below $T_N \approx 41$ K with a wave vector $\mathbf{k} = (0, \mathbf{k}_s, 1)$ in $Pbnm$ space group [9]. The value of incommensurate wave vector k_s at T_N was found to be 0.295, which gradually evolves with decreasing temperature, reaching the value of 0.28 at 30 K, and it remains constant below this temperature. BeCr_2O_4 orders at a temperature similar to that of TbMnO_3 in which the Mn^{3+} spins lock in at the commensurate value of k_s . In BeCr_2O_4 we find that the modulation vector is $(0, 0, 0.090(1))$ with the $Pbnm$ space group in the temperature range 26–7.5 K, and it changes to $(0, 0, 0.908(1))$ below 7.5 K with a larger monoclinic supercell. Although they have

some similarities, TbMnO_3 and BeCr_2O_4 have different magnetic lattices; the former has a three-dimensional magnetic lattice, while the latter possesses a quasi-two-dimensional sawtooth structure. Sawtooth multiferroics are very rare in the literature and thus only seldom investigated. An exception is the well-studied compound Mn_2GeO_4 , which also has an olivine-based crystal structure [33]. This compound exhibits successive magnetic phase transitions at $T_{N1} = 47$ K, $T_{N2} = 17$ K, and $T_{N3} = 5.5$ K similar to BeCr_2O_4 , which also shows three anomalies below 30 K. A substantial amount of lattice distortion was found at the transition temperatures in Mn_2GeO_4 where Mn^{2+} spins form sawtooths along the b axis. Different from the cycloidal order in the classic example of TbMnO_3 or in BeCr_2O_4 , a commensurate magnetic order with modulation vector $\mathbf{k} = (0, 0, 0)$ is established in Mn_2GeO_4 at high temperatures, which then transforms to a multicomponent magnetic structure when combined with an incommensurate ordering vector $(0.136(2), 0.211(2), 0)$ at low temperature. The spontaneous polarization developed in these compounds is ascribed to an incommensurate spiral order. BeCr_2O_4 , although a sawtooth latticelike Mn_2GeO_4 , is found in the present work to adopt an incommensurate magnetic order below the magnetic phase transition temperature at ~ 26 K. The propagation vector of $\mathbf{k} = (0, 0, 0.090(1))$

TABLE III. Structural data of magnetic unit cell of BeCr₂O₄ at 10 and 2 K, obtained from the Rietveld refinement of neutron diffraction data shown in Fig. 5.

Temperature (K)		10	2
Modulation vector (k)		(0, 0, 0.090(1))	(0, 0, 0.908(1))
Superspace group		<i>P21nm.1'(00g)0s0s</i>	<i>P21/a.1'[a](00g)00s</i>
Lattice parameters			
<i>a</i> (Å)		4.6812(3)	9.3320(7)
<i>b</i> (Å)		10.0581(1)	11.0577(8)
<i>c</i> (Å)		5.8076(1)	5.7885(4)
<i>V</i> (Å ³)		273.45(1)	541.5(1)
γ (deg)		90	114.956(2)
Atomic positions			
Cr1	<i>x/a</i>	0	0
	<i>y/b</i>	0	0
	<i>z/c</i>	0	0
Cr2	<i>x/a</i>	0.508(1)	-0.5
	<i>y/b</i>	0.224(1)	-0.5
	<i>z/c</i>	0.75	0
Cr3	<i>x/a</i>	-0.489(1)	-0.123(1)
	<i>y/b</i>	-0.235(1)	-0.771(1)
	<i>z/c</i>	-0.75	0.75
Cr4	<i>x/a</i>		-0.620(1)
	<i>y/b</i>		-0.267(1)
	<i>z/c</i>		0.75
<i>R</i> -factors	<i>R</i> _{obs}	3.84	4.64
	<i>wR</i> _{obs}	5.08	6.88

remained a constant down to T_{N1} . The arrangement of Cr³⁺ spins at the lowest temperature of our study is shown in Fig. 5(d).

Multiple nearby magnetic transitions are similarly observed in another sawtooth lattice multiferroic, Cu₃Nb₂O₈ [74]. Very similar to BeCr₂O₄, Cu₃Nb₂O₈ also shows a double peak in the specific heat [74]. This compound crystallizes in centrosymmetric triclinic symmetry, *P1*, but orders magnetically at 26 K and develops electric polarization stemming from the cycloidal magnetic order at 24 K. The magnetic order in the polar phase of Cu₃Nb₂O₈ has a propagation vector of $\mathbf{k} = (0.4879, 0.2813, 0.2029)$. An electric polarization of magnitude 17.8 $\mu\text{C m}^{-2}$ is observed almost perpendicular to the plane of rotation of the spins. This is in contradiction with the model predictions for electrical polarization in cycloidal multiferroics that should be contained within the plane in the case of coplanar spins. In the high-symmetry general cases, where the polarization is developed as a result of the DM interaction, the polarization develops in a direction perpendicular to both the magnetic propagation vector and the normal to the plane of rotation of the spins [22]. Contrary to the predictions for the cycloidal magnets, the polarization in Cu₃Nb₂O₈ lies perpendicular to the plane of the magnetic moments. This is explained as due to the coupling between a macroscopic structural rotation and the magnetically induced structural chirality [74]. These examples imply that a closer and more detailed understanding of the structural distortions

and rotations in sawtooth magnets, like BeCr₂O₄, is extremely instructive.

The multiple phase transitions observed in BeCr₂O₄ at low temperature lead to a slightly more complex magnetic-field-temperature phase diagram compared to that of atacamite Cu₂Cl(OH)₃, which also exhibits a sawtooth arrangement of spins [35]. The *H-T* phase diagram of this atacamite was determined up to high magnetic fields, up to 600 kOe. A complex magnetic phase evolution is seen in single-crystal samples of atacamite, where at 315 kOe, the magnetization isotherms attain a plateau. Interestingly, this plateau is argued not to be related to the magnetization plateau predicted in the magnetization of a spin-half sawtooth lattice, that is, the Δ chain [25]. Below the antiferromagnetic anomaly observed in the atacamite at 8.5 K, the compound enters a magnetically ordered state with a propagation vector equal to (1/2,0,1/2). It can be pointed out here that a weak low-temperature anomaly is observed in the specific heat of atacamite at approximately 5 K. This indicates a complex low-temperature magnetic phase, similar to what we are reporting here in the case of BeCr₂O₄. Moreover, a small value of magnetic entropy equal to 0.65*R* ln(2) is observed in atacamite at the transition temperature, hinting at the importance of the role of magnetic frustration. Judging from the magnetization curves presented in the current work on polycrystalline samples, it is clear that BeCr₂O₄ displays magnetic-field-dependent phase transitions below T_{N3} . Experiments on single crystals are essential to

reveal anisotropy effects in the magnetic response as well as the type of magnetic ordering in the temperature range $T_{N3} > T > T_{N2}$. High-magnetic-field response, in the range of 600 kOe or more, will be beneficial to examine if a magnetization plateau is also present in BeCr_2O_4 , and if so, how it compares with atacamite. Thus it is our immediate plan to investigate the high-field magnetic response of the magnetic structures of this compound using neutron diffraction experiments on large single crystals. Definitely, a comprehensive characterization of the electrical polarization and magnetoelectric effect in BeCr_2O_4 is highly warranted to explore multiferroicity in sawtooth lattices.

The bond angle Cr–O–Cr determined for BeCr_2O_4 is conducive for strong a superexchange mechanism between the Cr moments. Strong superexchange is known to be influential in bringing about induced multiferroicity in compounds like CuO and BiFeO_3 [66,75]. The systematic correlation between the Cu–O–Cu bond angle and the magnetic exchange interaction J is understood in the cuprates [76]. The importance of superexchange interaction in multiferroic compounds is highlighted in recent studies on the popular multiferroic compound BiFeO_3 [75]. The stereochemical activity of Bi's lone pair electrons alone cannot explain the observed electric polarization of BiFeO_3 . It is proposed that the Fe 3d orbitals render the compound a charge-transfer insulator, and the Fe–O–Fe superexchange enhances the developed electric polarization. The validity of this mechanism in the present compound BeCr_2O_4 and the extent to which it enhances the electric polarization remains to be investigated in detail.

V. CONCLUSIONS

Our study reveals multiple magnetic phase transitions in BeCr_2O_4 present below 26 K, which is identified as the magnetic phase transition temperature of this compound. A double-peak feature is observed (25 and 26 K) in the

physical properties of BeCr_2O_4 . The magnetic-field–temperature phase diagram indicates two antiferromagnetic phases, with possibly a complex phase region between the double-peak transitions. A noncollinear magnetic structure is estimated at low temperature for BeCr_2O_4 which supports the development of electric polarization through breaking of the inversion symmetry upon establishment of magnetic order. A reinvestigation of low-temperature magnetic phases, electric polarization, and high-magnetic-field responses of BeCr_2O_4 will be highly rewarding in the future.

ACKNOWLEDGMENTS

Use of the Advanced Photon Source at Argonne National Laboratory was supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Contract No. DE-AC02-06CH11357. A portion of this research used resources at the Spallation Neutron Source, a DOE Office of Science User Facility operated by the Oak Ridge National Laboratory. This work has been supported in part by the Croatian Science Foundation under Project No. IP-2020-02-9666. N.K.C.M. acknowledges the support of project Cryogenic Centre at the Institute of Physics-KaCf, cofinanced by the Croatian Government and the European Union through the European Regional Development Fund–Competitiveness and Cohesion Operational Programme (Grant No. KK.01.1.1.02.0012). The work at TU Wien was supported by the European Research Council (ERC Consolidator Grant No. 725521). The work at AGH University of Science and Technology was supported by the National Science Centre, Poland, Grant No. OPUS: UMO-2021/41/B/ST3/03454, the Polish National Agency for Academic Exchange under “Polish Returns 2019” Programme: PPN/PPO/2019/1/00014, and the subsidy of the Ministry of Science and Higher Education of Poland.

-
- [1] S.-W. Cheong and M. Mostovoy, *Nat. Mater.* **6**, 13 (2007).
 - [2] N. A. Spaldin and M. Fiebig, *Science* **309**, 391 (2005).
 - [3] N. A. Spaldin and R. Ramesh, *Nat. Mater.* **18**, 203 (2019).
 - [4] D. I. Khomskii, *J. Magn. Magn. Mater.* **306**, 1 (2006).
 - [5] K. Wang, J.-M. Liu, and Z. Ren, *Adv. Phys.* **58**, 321 (2009).
 - [6] H. Béa, M. Gajek, M. Bibes, and A. Barthélémy, *J. Phys.: Condens. Matter* **20**, 434221 (2008).
 - [7] I. E. Dzyaloshinskii, *Sov. Phys. JETP* **10**, 628 (1960).
 - [8] D. N. Astrov, *Sov. Phys. JETP* **11**, 708 (1960).
 - [9] T. Kimura, T. Goto, H. Shintani, K. Ishizaka, T. H. Arima, and Y. Tokura, *Nature (London)* **426**, 55 (2003).
 - [10] N. Terada, *J. Phys.: Condens. Matter* **26**, 453202 (2014).
 - [11] J. Van Den Brink and D. I. Khomskii, *J. Phys.: Condens. Matter* **20**, 434217 (2008).
 - [12] J. Wang, J. Neaton, H. Zheng, V. Nagarajan, S. Ogale, B. Liu, D. Viehland, V. Vaithyanathan, D. Schlom, U. Waghmare *et al.*, *Science* **299**, 1719 (2003).
 - [13] B. B. Van Aken, T. Palstra, A. Filippetti, and N. A. Spaldin, *Nat. Mater.* **3**, 164 (2004).
 - [14] S. Jodlauk, P. Becker, J. Mydosh, D. Khomskii, T. Lorenz, S. Streltsov, D. Hezel, and L. Bohatý, *J. Phys.: Condens. Matter* **19**, 432201 (2007).
 - [15] J. R. Sahu, C. R. Serrao, N. Ray, U. V. Waghmare, and C. Rao, *J. Mater. Chem.* **17**, 42 (2007).
 - [16] E. Pardo, C. Train, H. Liu, L.-M. Chamoreau, B. Dkhil, K. Boubekeur, F. Lloret, K. Nakatani, H. Tokoro, S. Ohkoshi *et al.*, *Angew. Chem. Int. Ed.* **51**, 8356 (2012).
 - [17] M. Fiebig, T. Lottermoser, D. Meier, and M. Trassin, *Nat. Rev. Mater.* **1**, 16046 (2016).
 - [18] D. Khomskii, *Physics* **2**, 20 (2009).
 - [19] M. Kenzelmann, A. B. Harris, S. Jonas, C. Broholm, J. Schefer, S. B. Kim, C. L. Zhang, S. W. Cheong, O. P. Vajk, and J. W. Lynn, *Phys. Rev. Lett.* **95**, 087206 (2005).
 - [20] H. Katsura, N. Nagaosa, and A. V. Balatsky, *Phys. Rev. Lett.* **95**, 057205 (2005).
 - [21] I. A. Sergienko and E. Dagotto, *Phys. Rev. B* **73**, 094434 (2006).
 - [22] M. Mostovoy, *Phys. Rev. Lett.* **96**, 067601 (2006).
 - [23] Y. Wang, W. B. Chen, F. Y. Liu, D. W. Yang, Y. Tian, C. G. Ma, M. D. Dramićanin, and M. G. Brik, *Results Phys.* **13**, 102180 (2019).
 - [24] R. E. Newnham, J. J. Kramer, W. A. Schulze, and L. E. Cross, *J. Appl. Phys.* **49**, 6088 (1978).
 - [25] K. Kubo, *Phys. Rev. B* **48**, 10552 (1993).

- [26] D. Sen, B. S. Shastry, R. E. Walstedt, and R. Cava, *Phys. Rev. B* **53**, 6401 (1996).
- [27] O. Le Bacq, A. Pasturel, C. Lacroix, and M. D. Núñez-Regueiro, *Phys. Rev. B* **71**, 014432 (2005).
- [28] H. Kikuchi, Y. Fujii, D. Takahashi, M. Azuma, Y. Shimakawa, T. Taniguchi, A. Matsuo, and K. Kindo, *J. Phys.: Conf. Ser.* **320**, 012045 (2011).
- [29] Y. Inagaki, Y. Narumi, K. Kindo, H. Kikuchi, T. Kamikawa, T. Kunimoto, S. Okubo, H. Ohta, T. Saito, M. Azuma *et al.*, *J. Phys. Soc. Jpn.* **74**, 2831 (2005).
- [30] A. Baniodeh, N. Magnani, Y. Lan, G. Buth, C. E. Anson, J. Richter, M. Affronte, J. Schnack, and A. K. Powell, *npj Quantum Mater.* **3**, 10 (2018).
- [31] H. O. Jeschke, H. Nakano, and T. Sakai, *Phys. Rev. B* **99**, 140410(R) (2019).
- [32] J. S. White, T. Honda, K. Kimura, T. Kimura, C. Niedermayer, O. Zaharko, A. Poole, B. Roessli, and M. Kenzelmann, *Phys. Rev. Lett.* **108**, 077204 (2012).
- [33] T. Honda, Y. Ishiguro, H. Nakamura, Y. Wakabayashi, and T. Kimura, *J. Phys. Soc. Jpn.* **81**, 103703 (2012).
- [34] T. Honda, J. White, A. Harris, L. Chapon, A. Fennell, B. Roessli, O. Zaharko, Y. Murakami, M. Kenzelmann, and T. Kimura, *Nat. Commun.* **8**, 15457 (2017).
- [35] L. Heinze, H. O. Jeschke, I. I. Mazin, A. Metavitsiadis, M. Reehuis, R. Feyerherm, J. U. Hoffmann, M. Bartkowiak, O. Prokhnenko, A. U. B. Wolter, X. Ding, V. S. Zapf, C. CorvalanMoya, F. Weickert, M. Jaime, K. C. Rule, D. Menzel, R. Valenti, W. Brenig, and S. Sullow, *Phys. Rev. Lett.* **126**, 207201 (2021).
- [36] V. P. Gnezdilov, Y. G. Pashkevich, V. S. Kurnosov, O. V. Zhuravlev, D. Wulferding, P. Lemmens, D. Menzel, E. S. Kozlyakova, A. Y. Akhrorov, E. S. Kuznetsova *et al.*, *Phys. Rev. B* **99**, 064413 (2019).
- [37] E. J. Bergholtz and Z. Liu, *Int. J. Mod. Phys. B* **27**, 1330017 (2013).
- [38] D. Leykam and S. Flach, *APL Photon.* **3**, 070901 (2018).
- [39] R. A. Vicencio, C. Cantillano, L. Morales-Inostroza, B. Real, C. Mejía-Cortés, S. Weimann, A. Szameit, and M. I. Molina, *Phys. Rev. Lett.* **114**, 245503 (2015).
- [40] V. O. Garlea, L. D. Sanjeeva, M. A. McGuire, P. Kumar, D. Sulejmanovic, J. He, and S.-J. Hwu, *Phys. Rev. B* **89**, 014426 (2014).
- [41] V. K. Gudelli, V. Kanchana, and G. Vaitheeswaran, *J. Phys.: Condens. Matter* **28**, 025502 (2016).
- [42] H. Nhalil, R. Baral, B. O. Khamala, A. Cosio, S. R. Singamaneni, M. Fitta, D. Antonio, K. Gofryk, R. R. Zope, T. Baruah *et al.*, *Phys. Rev. B* **99**, 184434 (2019).
- [43] R. Santoro and R. Newnham, *J. Am. Ceram. Soc.* **47**, 491 (1964).
- [44] P. R. Elliston and G. J. Troup, *Proc. Phys. Soc.* **92**, 1040 (1967).
- [45] J. H. Ranicar and P. R. Elliston, *Phys. Lett. A* **25**, 720 (1967).
- [46] D. E. Cox, B. C. Frazer, R. E. Newnham, and R. P. Santoro, *J. Appl. Phys.* **40**, 1124 (1969).
- [47] APEX3 v2018.7.2 2005-2018 Bruker AXS (1997).
- [48] A. Huq, M. Kirkham, P. F. Peterson, J. P. Hodges, P. S. Whitfield, K. Page, T. Hügle, E. B. Iverson, A. Parizzi, and G. Rennich, *J. Appl. Crystallogr.* **52**, 1189 (2019).
- [49] J. Rodriguez-Carvajal, Fullprof Suite, <http://www.ill.eu/sites/fullprof/> (2017).
- [50] V. Petříček, M. Dušek, and L. Palatinus, *Z. Kristallogr.–Cryst. Mater.* **229**, 345 (2014).
- [51] K. Momma and F. Izumi, *J. Appl. Crystallogr.* **44**, 1272 (2011).
- [52] N. A. Yamnova, S. M. Aksenov, L. A. Pautov, M. P. Popov, and Y. V. Erokhin, *Crystallogr. Rep.* **59**, 30 (2014).
- [53] L. A. Pautov, M. P. Popov, Y. V. Erokhin, V. V. Khiller, and V. Y. Karpenko, *Geol. Ore Deposits* **55**, 648 (2013).
- [54] I. D. Brown, *Struct. Bond. Cryst.* **2**, 1 (1981).
- [55] O. V. Kovalev, *Fiz. Tverd. Tela* **37**, 3382 (1995).
- [56] C. E. Weir and A. Van Valkenburg, *J. Res. Natl. Bur. Stand. A* **64**, 103 (1960).
- [57] K. Nawa, M. Avdeev, P. Berdonosov, A. Sobolev, I. Presniakov, A. Aslandukova, E. Kozlyakova, A. Vasiliev, I. Shchetinin, and T. J. Sato, *Sci. Rep.* **11**, 24049 (2021).
- [58] Y. Liu, L. D. Sanjeeva, V. O. Garlea, T. M. Smith Pellizzeri, J. W. Kolis, and A. S. Sefat, *Phys. Rev. B* **101**, 064423 (2020).
- [59] G. Morell, W. Perez, E. Ching-Prado, and R. S. Katiyar, *Phys. Rev. B* **53**, 5388 (1996).
- [60] C. Kittel, *Introduction to Solid State Physics* (Wiley New York, 1996).
- [61] J. M. Perez-Mato, S. V. Gallego, E. S. Tasci, L. Elcoro, G. de la Flor, and M. I. Aroyo, *Annu. Rev. Mater. Res.* **45**, 217 (2015).
- [62] Y. Tokura and S. Seki, *Adv. Mater.* **22**, 1554 (2010).
- [63] Y. Tokura, S. Seki, and N. Nagaosa, *Rep. Prog. Phys.* **77**, 076501 (2014).
- [64] T. Goto, T. Kimura, G. Lawes, A. P. Ramirez, and Y. Tokura, *Phys. Rev. Lett.* **92**, 257201 (2004).
- [65] K. Taniguchi, N. Abe, T. Takenobu, Y. Iwasa, and T. Arima, *Phys. Rev. Lett.* **97**, 097203 (2006).
- [66] T. Kimura, Y. Sekio, H. Nakamura, T. Siegrist, and A. Ramirez, *Nat. Mater.* **7**, 291 (2008).
- [67] Y. Yamasaki, S. Miyasaka, Y. Kaneko, J. P. He, T. Arima, and Y. Tokura, *Phys. Rev. Lett.* **96**, 207204 (2006).
- [68] K. Siratori, J. Akimitsu, E. Kita, and M. Nishi, *J. Phys. Soc. Jpn.* **48**, 1111 (1980).
- [69] T. Kimura, J. C. Lashley, and A. P. Ramirez, *Phys. Rev. B* **73**, 220401(R) (2006).
- [70] S. Seki, Y. Onose, and Y. Tokura, *Phys. Rev. Lett.* **101**, 067204 (2008).
- [71] N. Hur, S. Park, P. A. Sharma, J. S. Ahn, S. Guha, and S. W. Cheong, *Nature (London)* **429**, 392 (2004).
- [72] Y. Tokunaga, S. Iguchi, T. H. Arima, and Y. Tokura, *Phys. Rev. Lett.* **101**, 097205 (2008).
- [73] Y. Tokunaga, N. Furukawa, H. Sakai, Y. Taguchi, T.-h. Arima, and Y. Tokura, *Nat. Mater.* **8**, 558 (2009).
- [74] R. D. Johnson, S. Nair, L. C. Chapon, A. Bombardi, C. Vecchini, D. Prabhakaran, A. T. Boothroyd, and P. G. Radaelli, *Phys. Rev. Lett.* **107**, 137205 (2011).
- [75] Y. Shen, X. Wan, Q. Zhao, G. Li, and C.-G. Duan, *Phys. Rev. B* **104**, 024421 (2021).
- [76] T. Shimizu, T. Matsumoto, A. Goto, K. Yoshimura, and K. Kosuge, *J. Phys. Soc. Jpn.* **72**, 2165 (2003).

Correction: The omission of “Corresponding author” identifiers and email addresses for the last two authors has been fixed.