

# Study of the deamalgamation process in silver-tin-base amalgams

---

Dužević, Davor; Stubičar, Mirko; Milat, Ognjen; Tonejc, Antun; Trojko, Rudolf; Stubičar, Nada; Anić, Ivica; Stanković, Mirko

Source / Izvornik: **Fizika A, 1995, 4, 481 - 488**

Journal article, Published version

Rad u časopisu, Objavljena verzija rada (izdavačev PDF)

Permanent link / Trajna poveznica: <https://um.nsk.hr/um:nbn:hr:217:014344>

Rights / Prava: [In copyright](#)/[Zaštićeno autorskim pravom.](#)

Download date / Datum preuzimanja: **2024-09-14**



Repository / Repozitorij:

[Repository of the Faculty of Science - University of Zagreb](#)



STUDY OF THE DEAMALGAMATION PROCESS IN SILVER-TIN-BASE  
AMALGAMS <sup>1</sup>

DAVOR DUŽEVIĆ<sup>a</sup>, MIRKO STUBIČAR<sup>b</sup>, OGNJEN MILAT<sup>c</sup>, ANTUN TONEJC<sup>b</sup>,  
RUDOLF TROJKO<sup>d</sup>, NADA STUBIČAR<sup>b</sup>, IVICA ANIĆ<sup>e</sup> and MIRKO STANKOVIĆ<sup>b</sup>

<sup>a</sup> *Faculty of Textile Technology, University of Zagreb, Croatia*

<sup>b</sup> *Faculty of Science, University of Zagreb, Croatia*

<sup>c</sup> *Institute of Physics of the University, Zagreb, Croatia*

<sup>d</sup> *Rugjer Bosković Institute, Zagreb, Croatia*

<sup>e</sup> *School of Dentistry, University of Zagreb, Croatia*

**Dedicated to Professor Mladen Paić on the occasion of his 90<sup>th</sup> birthday**

Received 4 January 1995

Revised manuscript received 1 August 1995

UDC 539.213

PACS 82.80.-d

Deamalgamation of the common dentistry amalgam scrap, as well as of a model Ag<sub>70</sub>Sn<sub>17</sub>Cu<sub>13</sub> prealloy amalgam, was studied by metallography, microhardness, X-ray diffraction and differential thermal analysis techniques. The results are discussed from the view-point of the possible powder-metallurgical application of the process.

### *1. Introduction*

The use of metal powders for dental purposes represents one of the oldest technical applications of powder metallurgy [1]. On the other side, the so-called amalgam

---

<sup>1</sup>The paper was presented at the Third Slovenian-Croatian Crystallographic Meeting (Kranjska Gora, Slovenia, Sept. 29-30, 1994).

process [2-5] played a significant role in the early history of tungsten powder metallurgy. The Cd-Bi amalgam served as a binder to refractory tungsten-powder in production of incandescent lamp filaments. In that process the amalgam was completely expelled from refractory tungsten matrix at subsequent high-temperature sintering of the green compact. Although obsolete, this process, in a slightly modified version, may still have the virtue appealing for its revival. In fact, it could prove worthy to distil-off fractionally mercury alone from the amalgam binder of a refractory powder matrix and to keep the amalgam prealloy rest as the solid metallic binder of the consolidated body. The key prerequisite to approach this renewed amalgam process efficiently is to study the deamalgamation in relation to crystallographic, physical, mechanical and chemical properties of the deamalgamated metallic or intermetallic products, as well as to their metallurgical and structural compatibility with promising refractory powder matrices. Besides, the study of deamalgamation process of dentistry scrap should obviously bear very positive ecological implications.

## 2. *Experimental*

We designed and constructed the simple vacuum distillation apparatus, shown in Fig. 1 [6], which was used for the deamalgamation experiments.

Processing parameters were adjusted by treating the unsorted amalgam filling scrap with a minor share of retrieved restoratives from a dentistry laboratory. An optimized temperature-time diagram for a 50 g amalgam scrap charge is shown in Fig. 2.

The synthesis of a representative  $\text{Ag}_{70}\text{Sn}_{17}\text{Cu}_{13}$  (weight percentages) prealloy was made to ensure compositionally well defined and highly practice-matching research material. The highly homogenized mixture of 99.9<sup>+</sup> wt.% pure component metal powders was encapsulated into a quartz tube, evacuated to  $10^{-3}$  Pa, melted at 1120 K, and filed down to a fine powder. The X-ray diffraction (XRD) of powders was performed using a Philips PW 1820 diffractometer with  $\text{CuK}_{\alpha}$  graphite-monochromated radiation. For identification of the phases present in the samples, we used the data collected in Ref. 7. Specimens for metallographic observation and for determination of Vickers microhardness were prepared by a standard mechanical polishing procedure. A Leitz light microscope, Aristomet type, supplied with an automatic camera, was used to record the microstructure in specimens. Also, a Leitz Metallux 3 microscope in conjunction with Miniload 2 type attachment, supplied with the RZD DO computing device, was used for microhardness determination. The pyramide load during the measurement was 0.981 N. Differential thermal analysis (DTA) was performed by means of a Gebruder Netsch equipment. All DTA measurements were made in a helium atmosphere applying a heating rate of 5 K/min.

## 3. *Results and discussion*

The microstructure of amalgam scrap observed in the specimens before and after deamalgamation is shown in Figs. 3a and b and (c and d), respectively.

The micrographs (e and f) in the same figure represent microstructure observed in the model Ag<sub>70</sub>-Sn<sub>17</sub>-Cu<sub>13</sub> prealloy. The corresponding hardness numbers for the above mentioned alloys are included in Table 1.

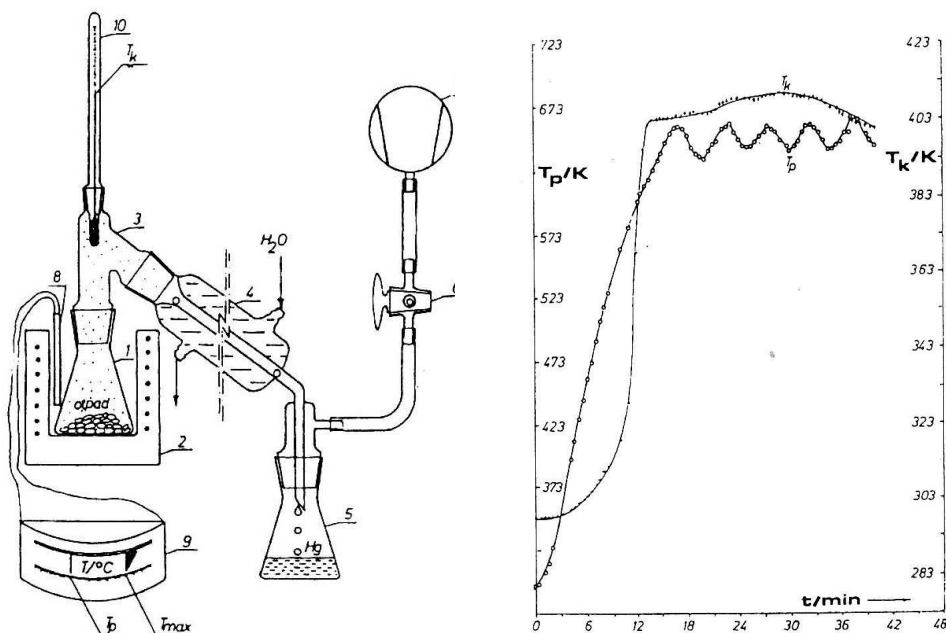


Fig. 1. Schematic drawing of the deamalgamation equipment; legend: glass container - 1, pot furnace - 2, joining glass piece - 3, vapour condenser - 4, glass container for liquid Hg - 5, two-way valve - 6, vacuum pump - 7, thermocouple ( $T_p$ ) - 8, temperature controller and display - 9, and mercury thermometer ( $T_k$ ) - 10.

Fig. 2. The temperature-time diagram for a 50 g amalgam scrap charge. Temperatures  $T_p$  and  $T_k$  were measured by thermocouple and by mercury thermometer (right).

The obvious cause of the significant decrease of hardness on deamalgamation is an enormous population of pores of an average diameter of about 10  $\mu\text{m}$  in the deamalgamated specimen (see Figs. 3c and d).

TABLE 1.  
Vickers microhardness determined on studied samples.

Amalgam scrap	(1.09 + 0.24) GPa
Deamalgamated amalgam scrap	(0.45 + 0.08) GPa
Model alloy Ag <sub>70</sub> Sn <sub>17</sub> Cu <sub>13</sub>	(1.40 + 0.17) GPa

When preparing an amalgam tooth filling ("trituration"), one admixes small quantity of prealloyed metallic powder and approximately the same mass of liquid

mercury. It is known that the microstructure of a typical low-copper Ag-Sn-base amalgam (LCA) consists of roughly 30 vol.% of unconsumed prealloy  $\gamma$ -Ag<sub>3</sub>Sn particles embedded in minute  $\gamma_1$ -Ag<sub>2</sub>Hg<sub>3</sub> grains participating with about 60 vol.%, and of about 10 vol.% of irregular discrete  $\gamma_2$ -Sn<sub>7</sub>Hg grains [8]. A simple calculation

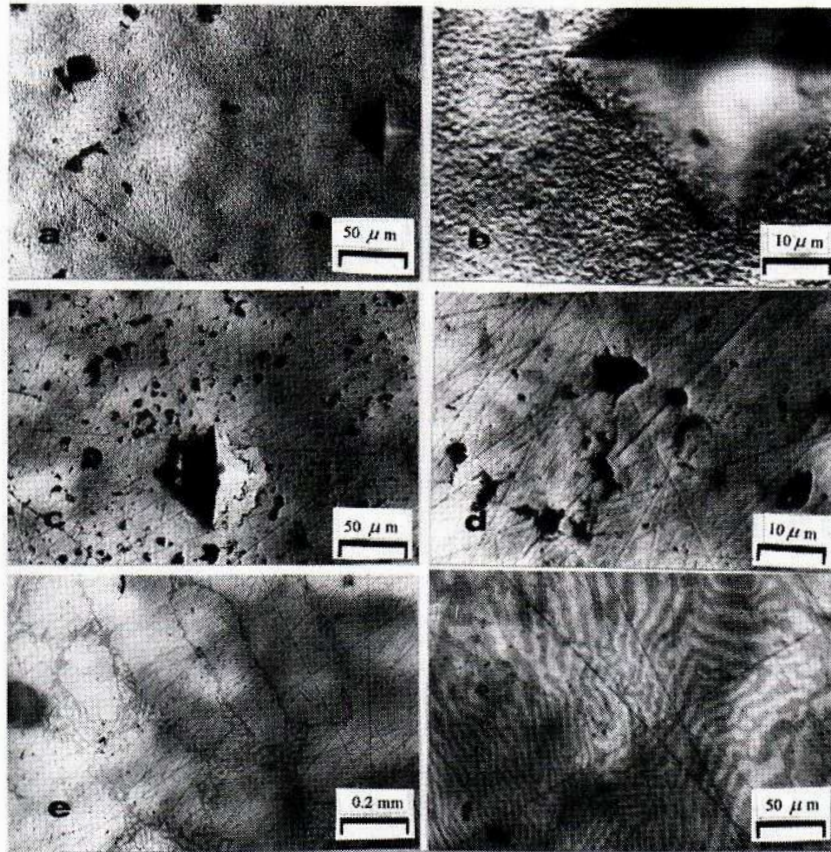


Fig. 3. Light micrographs of a dental amalgam scrap (a and b), of a deamalgamated dental amalgam scrap (c and d), and of a model Ag<sub>70</sub>Sn<sub>17</sub>Cu<sub>13</sub> prealloy (e and f), at two magnifications, respectively.

shows that mercury should be completely structurally engaged in these phases after setting, i.e. no free mercury in the amalgam should exist. Beside the microstructure uniformity (Figs. 3a and b), this statement supports the XRD pattern of amalgam scrap filings, exhibiting sharp diffraction lines, identified as:  $\gamma_1$ -Ag<sub>2</sub>Hg<sub>3</sub> ([7], card number: 11-67), Cu<sub>7</sub>Hg<sub>6</sub> ([7], card number: 33-470), and  $\zeta$ -Cu<sub>6</sub>Sn<sub>5</sub> ([7], card number: 2-713) (see Fig. 4a). In the same figure two lines which do not belong to the above phases are denoted by x. Hence, the origin of the cavities in the deamalgamated samples observed in Figs. 3c and d cannot be explained by assuming that

they were the emptied space of former free-mercury wells. These cavities are due to a kind of "internal shrinkage", whose nucleation and growth mechanisms challenge for a rational explanation.

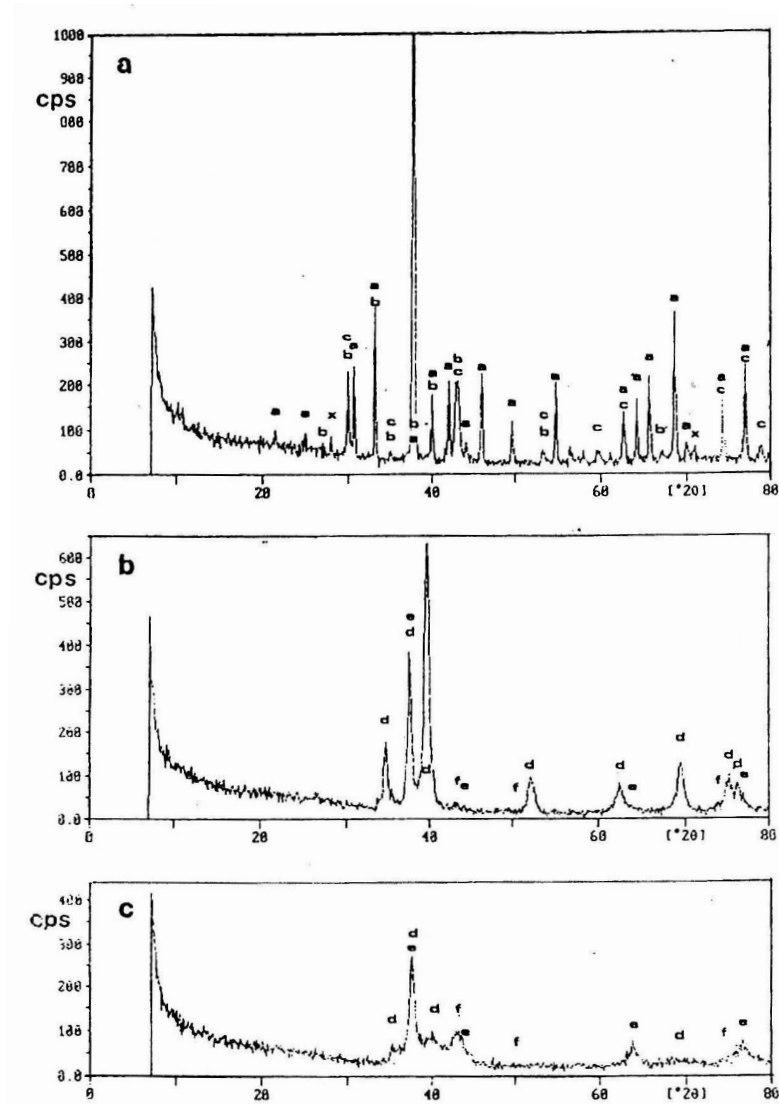


Fig. 4. XRD patterns of a dental amalgam scrap before (a) and after deamalgamation (b), and of the model Ag<sub>70</sub>Sn<sub>17</sub>Cu<sub>13</sub> prealloy (c), respectively. The angular positions of observed diffraction lines belonging to the  $\gamma_1$ -Ag<sub>2</sub>Hg<sub>3</sub>, Cu<sub>7</sub>Hg<sub>6</sub>,  $\zeta$ -Cu<sub>6</sub>Sn<sub>5</sub>,  $\gamma$ -Ag<sub>3</sub>Sn, Ag and Cu phases are marked by a, b, c, d, e and f, respectively.

The mass loss in the deamalgamation procedure applied was on the average 50% of the input amalgam scrap charge which means that the process of deamalgamation goes to completion (or at least very nearly so). This statement is convincingly confirmed by XRD pattern taken from a deamalgamated sample (Fig. 4b). The observed diffraction pattern belongs entirely to the  $\gamma$ -Ag<sub>3</sub>Sn prealloy phase (the expected slight marks of the strongest Cu- and Ag-lines in the pattern indicate an LCA prealloy composition). This observation leads to an important conclusion that the deamalgamation process does not affect the phase structure of the original prealloy powder. In other words, the amalgamation is a reversible crystallographical process. This is decisive for the renewed amalgam process mentioned in Introduction. One can generally rely upon the expectation that the original crystal structure of the amalgam prealloy binder within a refractory powder compact matrix will not dramatically change after deamalgamation. This is a base for programming the material's properties.

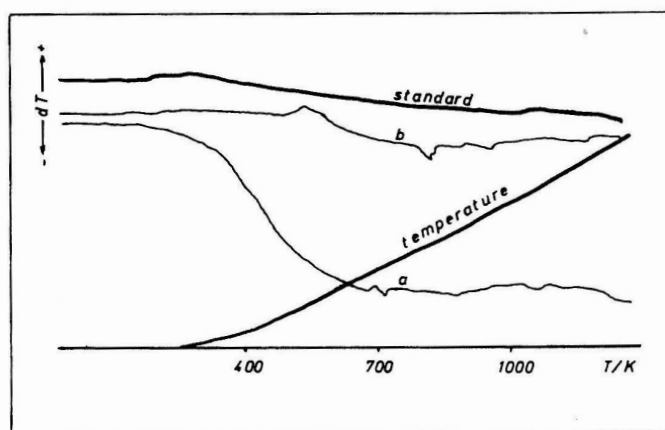


Fig. 5. DTA curves of a deamalgamated dental amalgam scrap (a), of the Ag<sub>70</sub>Sn<sub>17</sub>Cu<sub>13</sub> prealloy (b), and the curve denoted "standard" representing the run without sample in place.

Naturally, this general prospect comprises a number of problems that should be solved. For example, with regard to the compactness and the mechanical properties of the deamalgamated binder, one should interpret unusually large endothermic slope in the DTA diagram of deamalgamated sample (curve a in Fig. 5), beginning practically at room temperature and ending at a temperature of nearly 700 K. An apparently logical doubt about the rest-mercury evaporation is inconsistent within the previously represented facts. The actual origin of XRD line broadening of the  $\gamma$ -Ag<sub>3</sub>Sn phase (see Fig. 4b) has also to be rationalized. It was very easy to prepare filings for XRD analysis, and this cannot be considered as a possible cause of broadening. One balances between the rather narrow compositional range (26.0–26.7 mass % Sn) of this intermetallide and the eventual powder particle comminution upon deamalgamation as the possible causes, and this is the puzzle to be

considered carefully.

Micrographs in Figs. 3e and f show the microstructure of the vacuum melted model high-copper-single-composition (HCSC)  $\text{Ag}_{70}\text{Sn}_{17}\text{Cu}_{13}$  amalgam prealloy. It is highly compact and uniform and is harder than the amalgam itself (see Table 1). XRD pattern of this prealloy (Fig. 4c) confirms the expectation that the dominating grains (of 5 to 100  $\mu\text{m}$  in diameter) belong to the Ag-base solid solution, while the minor grain-boundary phases are identified as  $\gamma\text{-Ag}_3\text{Sn}$  and pure Cu. In this case the XRD line broadening is probably a consequence of very difficult sample preparative filing. The corresponding DTA diagram (curve b in Fig. 5) shows some interesting details of both the endo- and exothermic nature, but the most important information obtained from DTA measurement seems to be the absence of the large downward slope at low temperatures. The difference in DTA behaviour of deamalgamated and original amalgam prealloy, curves (a) and (b) in Fig. 5, calls for further investigation.

#### 4. Conclusion

Our results point to the following conclusions: The efficiency of a simple vacuum distillation system has been successfully tested. The processing parameters of the procedure applied were properly optimized by using the dentistry filling amalgam scraps and retrieved restoratives as testing materials. The amalgamation process proves crystallographically reversible, i.e. the original prealloy crystal structure gets restored on deamalgamation. Beside these positive statements mentioned above a number of unanswered questions, like “internal shrinkage” or endothermic slope, should be explained. Furthermore, the reaction between the liquid mercury and the fine Ag-Sn-Cu-base prealloy powder should be considered as a process of liquid phase sintering with a transient liquid phase in which mercury is used in the reaction [4,9]. Therefore, answering this and similar questions will promote an economic and comfortable study of sintering process at room temperature, which otherwise occurs at high- temperatures, as well as applications of the obtained results, particularly regarding the sintering procedure, to other available and promising systems.

#### Acknowledgement

The authors are grateful to the referee whose valuable suggestions clarified greatly the manuscript. The Ministry of Science and Technology of the Republic of Croatia is acknowledged for financial support.

#### References

- 1) T. Okabe, *Setting Mechanism of Dental Amalgam*, in: *Proceedings of a Symposium on Setting Mechanisms of Dental Materials*, Ed. by D. C. Watts, Cameron House, Loch Lommond Scotland, June 30, 1992;



- 2) C. G. Goetzl, *Treatise on Powder Metallurgy*, Vol. II (Interscience Publishers Inc., New York/London, 1950);
- 3) R. Kieffer and W. Hotop, *Pulvermetallurgie und Sinterwerkstoffe* (Berlin, 1943);
- 4) F. V. Lenel, *Powder Metallurgy Principles and Applications* (Metal Powder Industries Federation, Princeton/New Jersey, 1980);
- 5) F. Skaupy, *Metallkeramik* (Verlag Chemie GmbH, Weinheim/Bergstrasse, 1950);
- 6) Patent Application Nr. 381-03/94-01/23051, State Patent Office of the Republic of Croatia, Zagreb, Aug. 16, 1994;
- 7) *Selected Powder Diffraction Data for Metals and Alloys*, 1.ed., Vol. 1 and 2 (International Center for Diffraction Data, Swarthmore, 1978);
- 8) D. B. Mahler and J. D. Adey, *J. Dent. Res.* **70** (1991) 1384;
- 9) C. Reynolds Jr. and H. G. F. Wilsdorf, *J. Biomed. Mater. Res.* **9** (1975) 335.

#### ISTRAŽIVANJE DEAMALGAMACIJSKOG PROCESA U AMALGAMIMA SLITINA BOGATIH SREBROM I KOSITROM

Proces deamalgamacije u amalgamima slitina bogatih srebrom i kositrom istraživan je metalografijom, mjerenjem mikrotvrdoće, rentgenskom difrakcijom i diferencijalnom termičkom analizom. Dobiveni rezultati raspravljani su s gledišta regeneracije otpadnog amalgama (reciklaže, tj. obnavljanja strukture i svojstava polaznih komponenti), kao i moguće uporabe ovog procesa u metalurgiji praha.