

Short-wavelength cutoff effects in the ac fluctuation conductivity of superconductors

Peligrad, D.-N.; Mehring, M.; Dulčić, Antonije

Source / Izvornik: **Physical review B: Condensed matter and materials physics**, 2003, 67

Journal article, Published version

Rad u časopisu, Objavljena verzija rada (izdavačev PDF)

<https://doi.org/10.1103/PhysRevB.67.174515>

Permanent link / Trajna poveznica: <https://um.nsk.hr/um:nbn:hr:217:061457>

Rights / Prava: [In copyright](#) / [Zaštićeno autorskim pravom.](#)

Download date / Datum preuzimanja: **2025-02-05**



Repository / Repozitorij:

[Repository of the Faculty of Science - University of Zagreb](#)



Short-wavelength cutoff effects in the ac fluctuation conductivity of superconductors

D.-N. Peligrad* and M. Mehring†

2. Physikalisches Institut, Universität Stuttgart, 70550 Stuttgart, Germany

A. Dulčić‡

Department of Physics, Faculty of Science, University of Zagreb, P.O. Box 331, 10002 Zagreb, Croatia

(Received 28 February 2002; revised manuscript received 26 November 2002; published 21 May 2003)

The short-wavelength cutoff has been introduced in the calculation of the ac fluctuation conductivity of superconductors. It is shown that a finite cutoff leads to a breakdown of the scaling property in frequency and temperature. Also, it increases the phase ϕ of the complex conductivity ($\tan \phi = \sigma_2 / \sigma_1$) beyond $\pi/4$ at T_c . Detailed expressions containing all essential parameters are derived for three-dimensional isotropic and anisotropic fluctuation conductivity. In the two-dimensional case we obtain individual expressions for the fluctuation conductivity for each term in the sum over discrete wave vectors perpendicular to the film plane. A comparison of the theory to the experimental microwave fluctuation conductivity is provided.

DOI: 10.1103/PhysRevB.67.174515

PACS number(s): 74.40.+k, 74.25.Nf, 74.78.Bz

I. INTRODUCTION

Fluctuations of the order parameter near the critical temperature T_c are much larger in high- T_c superconductors than in classical low-temperature superconductors. One of the reasons lies in the higher thermal energy $k_B T_c$ which provides the excitations and the other in the very short coherence lengths which occur in high- T_c cuprate superconductors. With these properties, the region of critical fluctuations was estimated from the Ginzburg criterion to be of the order of 1 K or more, around T_c , which renders the critical region accessible to experimental investigations.¹ Farther above T_c , one expects to observe the transition from critical to noninteracting Gaussian fluctuations which are the lowest-order fluctuation corrections to the mean-field theory.²

The layered structure of high- T_c superconductors requires some theoretical sophistication. One could treat these superconductors with various models from three-dimensional (3D) anisotropic to coupled layer Lawrence-Doniach models or purely two-dimensional (2D) ones. Due to the temperature variation of the coherence lengths, one could even expect a dimensional crossover in some systems. The fluctuation conductivity is altered by dimensionality in various models so that a detailed comparison of model calculations and experimental data could address the dimensionality problem.

For the reasons stated above, the fluctuation conductivity in high- T_c superconductors was studied experimentally by many authors^{3–14} Most of them used dc resistivity measurements.^{3–5,9–14} The reports were controversial in their conclusions about the dimensionality of the system and the critical exponents. It has been shown that, in a wide temperature range above T_c , the fluctuation conductivity did not follow any of the single-exponent power laws predicted by scaling and mean-field theories.⁵ The data in the Gaussian regime could be fitted by an expression derived within the Ginzburg-Landau (GL) theory with a short-wavelength cutoff in the fluctuation spectrum. Recently, Silva *et al.*¹³ have proved that the GL approach with an appropriate choice of cutoff parameter yields a result which is identical to that of the microscopic Aslamazov-Larkin (AL) approach with re-

duced excitations of the short-wavelength fluctuations.¹⁵ It has been further shown that the detailed temperature dependence of the fluctuation conductivity was not universal, but sample dependent. In this respect, the GL approach has practical advantages since the cutoff parameter can be readily adjusted in fitting the experimental data. Silva *et al.*¹³ could fit very well the data on a number of single crystals in the Gaussian region from $T_c + 1$ K to $T_c + 25$ K.

When critical fluctuations are studied, it becomes essential to know accurately the value of T_c . However, the determination of T_c from dc resistivity measurements brings about some uncertainties. One should avoid the use of unjustifiable definitions of T_c such as, e.g., (i) zero-resistance temperature, (ii) midpoint of the transition, (iii) maximum of the derivative $d\rho/dT$, (iv) intersection of the tangent to the transition curve with the temperature axis, etc. The correct value of the critical temperature can be determined as an additional fitting parameter in the analysis of the fluctuation conductivity. Usually one assumes that a well-defined power law holds in a given narrow temperature range and then determines both T_c and the critical exponent from the selected segment.^{10,12,14} However, the experimental data usually show an almost continuous change of slope so that the uncertainty in the determination of T_c is an unsolved problem. Besides, the effects of the cutoff have been neglected in the analysis of data close to T_c . Even though the values of the fluctuation conductivity near T_c are not much affected by the introduction of the cutoff, the slopes can be considerably changed,⁴ and the analysis may become uncertain.

A number of microwave studies have been reported showing clear signs of fluctuations in both the real and imaginary parts of the ac conductivity.^{6,7,16–18} The real part σ_1 of the complex conductivity ($\tilde{\sigma} = \sigma_1 - i\sigma_2$) has a sharp peak at T_c , which is not observed in, e.g., Nb as representative of low-temperature classical superconductors.¹⁹ The salient feature of the ac case is that the fluctuation conductivity does not diverge at T_c because a finite frequency provides a limit to the observation of the critical slowing down near T_c . The determination of T_c from the peak in σ_1 is a reasonable

choice.⁶ It is also important to note that σ_1 and σ_2 have individually different temperature and frequency dependences, even though they result from the same underlying physics. Testing a given theoretical model becomes more stringent when two curves have to be fitted with the same set of parameters.

The expressions for the ac fluctuation conductivity in the Gaussian regime have been deduced within the time-dependent Ginzburg-Landau (TDGL) theory of Schmidt.²⁰ Using general physical arguments, Fisher, Fisher, and Huse²¹ provided a formulation for the scaling of the complex ac conductivity as

$$\tilde{\sigma}(\omega) \propto \xi^{z+2-D} \tilde{\mathcal{S}}_{\pm}(\omega \xi^z), \quad (1)$$

where ξ is the correlation length, z is the dynamical critical exponent, D is the dimensionality of the system, and $\tilde{\mathcal{S}}_{\pm}(\omega \xi^z)$ are some complex scaling functions above and below T_c . This form of fluctuation conductivity was claimed to hold in both the Gaussian and critical regimes. Dorsey²² has deduced the scaling functions in the Gaussian regime above T_c and verified the previous results of Schmidt.²⁰ More recently, Wickham and Dorsey²³ have shown that even in the critical regime, where the quartic term in the GL free energy plays a role, the scaling functions preserve the same form as in the Gaussian regime.

The above-mentioned theoretical expressions of the ac fluctuation conductivity did not take into account the slow variation approximation which is required for the validity of the Ginzburg-Landau theory.² It was noted a long time ago that the summation over the fluctuation modes had to be truncated at a wave vector which corresponded roughly to the inverse of the intrinsic coherence length ξ_0 .²⁴ The improved treatment with a short-wavelength cutoff was applied in fluctuation diamagnetism,²⁵ and dc paraconductivity far above T_c .²⁶ This approach was also applied in dc fluctuation conductivity of high- T_c superconductors where one encounters a large anisotropy.^{4,5,13} Introduction of the short-wavelength cutoff was found to be essential in fitting the theoretical expressions to the experimental data. In view of the great potential of the microwave method described above, we find motivation to elaborate in this paper the improved theory of ac fluctuation conductivity including the short-wavelength cutoff. We find that the resulting expressions can be written in the form of Eq. (1). However, the cutoff introduces a breakdown of the scaling property in the variable $\omega \xi^z$. Also, we find that the phase ϕ of the complex conductivity ($\tan \phi = \sigma_2 / \sigma_1$) evaluated at T_c departs from the value $\pi/4$ when a cutoff is introduced. Values of ϕ larger than $\pi/4$ were observed experimentally,⁷ but were attributed to an unusually large dynamic critical exponent. Also, deviation of the scaling in the variable $\omega \xi^z$ was observed already at 2 K above T_c ,⁷ but no analysis was made considering the short-wavelength cutoff in the fluctuation spectrum. The present theory is developed for different dimensionalities which facilitates comparison with experimental data.

II. EFFECTS OF THE SHORT-WAVELENGTH CUTOFF

Frequency-dependent conductivity can be calculated within the Kubo formalism from the current correlation function. For the fluctuation conductivity one has to consider the current due to the fluctuations of the order parameter. The resulting expression for the real part of the conductivity is²⁷

$$\sigma_1^{xx} = \left(\frac{2e\hbar}{m} \right)^2 \frac{1}{k_B T} \sum_{\mathbf{k}} k_x^2 \langle |\psi_{\mathbf{k}}|^2 \rangle^2 \frac{\tau_k/2}{1 + (\omega \tau_k/2)^2}, \quad (2)$$

where the current is assumed to be in the x direction. $\psi_{\mathbf{k}}$ is the Fourier component of the order parameter, and $\tau_k = \tau_0 / (1 + \xi^2 k^2)$ is the relaxation time of the k th component. The relaxation time for the $k=0$ mode is given by

$$\tau_0 = \frac{\pi\hbar}{8k_B T_c} \left(\frac{\xi(T)}{\xi_0} \right)^z, \quad (3)$$

where z is the dynamic critical exponent. An alternative approach is to calculate the response of the system to an external field through the expectation value of the current operator averaged with respect to the noise.^{22,28,29}

Equation (2) is obtained from the time-dependent Ginzburg-Landau theory and represents the equivalent of the Aslamazov-Larkin fluctuation conductivity obtained from microscopic calculations. In the following, we present the results which take account of the short-wavelength cutoff in this contribution to the ac fluctuation conductivity. The other contributions such as Maki-Thomson (MT) and one-electron density of states (DOS) renormalization³⁰⁻³² cannot be treated within the time-dependent Ginzburg-Landau theory but require microscopic calculations. It has been shown³¹ that the MT anomalous contribution in high- T_c superconductors is almost temperature independent while the DOS contribution is strongly temperature dependent and contains a number of parameters which have to be determined through a complex fitting procedure in an experimental data analysis.³³ Since the three terms in the fluctuation conductivity are additive, it is important to have the Aslamazov-Larkin term corrected for the short-wavelength cutoff which then allows us to fit the MT and DOS contributions properly from the rest of the total experimental fluctuation conductivity.

The sum in Eq. (2) can be evaluated by integration considering the appropriate dimensionality. In this section we discuss the simplest case of an isotropic 3D superconductor. Integration in \mathbf{k} space needs a cutoff since the order parameter cannot vary appreciably over distances which are shorter than some minimum wavelength. The cutoff in k_x can be expressed as $k_x^{max} = \Lambda / \xi_0$, where Λ is a dimensionless cutoff parameter. Obviously, $\Lambda \rightarrow \infty$ would imply no cutoff in the integration, whereas for $\Lambda \approx 1$ one obtains the usually assumed cutoff at $1/\xi_0$. In the 3D isotropic case, the same cutoff applies also to k_y and k_z so that for the 3D integration in \mathbf{k} space one has to set the cutoff limit for the modulus $k^{max} = \sqrt{3}\Lambda / \xi_0$. With the change of variable $q(T) = k\xi(T)$ one obtains

$$\sigma_1^{3D,iso}(\omega, T, \Lambda) = \frac{e^2}{6\pi\hbar\xi_0} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1} \times \int_0^Q \frac{q^4}{(1+q^2)[\Omega^2+(1+q^2)^2]} dq, \quad (4)$$

where

$$Q(T, \Lambda) = k_{cut}\xi(T) = \sqrt{3}\Lambda \left(\frac{\xi(T)}{\xi_0} \right) \quad (5)$$

is the temperature-dependent cutoff limit in q space and

$$\Omega(\omega, T) = \frac{\omega\tau_0}{2} = \frac{\pi}{16} \frac{\hbar\omega}{k_B T_c} \left(\frac{\xi(T)}{\xi_0} \right)^z \quad (6)$$

is a dimensionless variable which depends on frequency and temperature as independent experimental variables.

For the dc case ($\omega=0$) and no cutoff ($\Lambda \rightarrow \infty$), one finds from Eq. (4)

$$\sigma_{dc}^{3D,iso}(T, \Lambda \rightarrow \infty) = \frac{e^2}{32\hbar\xi_0} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1}, \quad (7)$$

which reduces to the well-known Aslamazov-Larkin result²⁷ provided that relaxational dynamics is assumed ($z=2$) and $\xi(T)/\xi_0$ is taken only in the Gaussian limit as $1/\sqrt{\epsilon}$. However, with a finite cutoff parameter Λ one obtains

$$\sigma_{dc}^{3D,iso}(T, \Lambda) = \frac{e^2}{16\pi\hbar\xi_0} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1} \times \left[\arctan(Q) - Q \frac{(\frac{5}{3}Q^2+1)}{(1+Q^2)^2} \right]. \quad (8)$$

This result has been obtained by Hopfengärtner *et al.*⁴ except that they used only the Gaussian limit $1/\sqrt{\epsilon}$ for the reduced correlation length $\xi(T)/\xi_0$. Their analysis has shown that the cutoff plays no role exactly at T_c since $Q \rightarrow \infty$ regardless of Λ . However, at any temperature above T_c one gets a finite Q and the value of the conductivity is lowered with respect to the result given by Eq. (7). Their conclusion was that the Gaussian fluctuations with no cutoff yield an overestimated fluctuation conductivity.

In this paper we are primarily interested in the ac case. Before integrating Eq. (4) with $\Omega \neq 0$, we find the corresponding expression for the imaginary part σ_2 . We can apply Kramers-Kronig relations to each of the Fourier components in Eq. (2) and carry out the summation. This is equivalent to a calculation of the kernel \mathcal{K}_2 for σ_2 from the kernel \mathcal{K}_1 used in Eq. (4), namely,

$$\mathcal{K}_2(\Omega) = \frac{2\Omega}{\pi} \int_0^\infty \frac{\mathcal{K}_1(\Omega')}{\Omega^2 - \Omega'^2} d\Omega'. \quad (9)$$

With the kernel $\mathcal{K}_2(\Omega)$, the imaginary part of the fluctuation conductivity can be calculated for any cutoff parameter Λ :

$$\sigma_2^{3D,iso}(\omega, T, \Lambda) = \frac{e^2}{6\pi\hbar\xi_0} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1} \times \int_0^Q \frac{\Omega q^4}{(1+q^2)^2[\Omega^2+(1+q^2)^2]} dq. \quad (10)$$

Finally, the complex fluctuation conductivity can be written in the form

$$\tilde{\sigma}^{3D,iso}(\omega, T, \Lambda) = \frac{e^2}{32\hbar\xi_0} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1} [\mathcal{S}_1^{3D,iso}(\omega, T, \Lambda) + i\mathcal{S}_2^{3D,iso}(\omega, T, \Lambda)]. \quad (11)$$

The prefactor is equal to the dc result with no cutoff effect as in Eq. (7). The functions $\mathcal{S}_{1,2}$ are given by the expressions

$$\mathcal{S}_1^{3D,iso}(\omega, T, \Lambda) = \frac{1}{3\pi\Omega^2} [P_-(P_+^2+2)L + 2P_+(P_-^2-2)A + 16 \arctan(Q)], \quad (12)$$

$$\mathcal{S}_2^{3D,iso}(\omega, T, \Lambda) = \frac{1}{3\pi\Omega^2} \left[2P_-(P_+^2+2)A - P_+(P_-^2-2)L - 24\Omega \arctan(Q) + 8\Omega \frac{Q}{1+Q^2} \right], \quad (13)$$

where we used the following shorthand notation:

$$P_\pm = \sqrt{2} \sqrt{\sqrt{\Omega^2+1} \pm 1}, \quad (14)$$

$$L = \ln \left(\frac{2+Q^2+(Q-P_-)^2}{2+Q^2+(Q+P_-)^2} \right), \quad (15)$$

$$A = \arctan \left(\frac{2Q+P_-}{P_+} \right) + \arctan \left(\frac{2Q-P_-}{P_+} \right). \quad (16)$$

It can be easily verified that the $\mathcal{S}_{1,2}$ functions given by Eq. (12) and Eq. (13) have proper limits. In the dc limit ($\Omega \rightarrow 0$), one finds that $\mathcal{S}_2 \rightarrow 0$, and \mathcal{S}_1 leads to the dc result of Eq. (8). One can also verify that the ac results obtained previously by Schmidt²⁰ and Dorsey²² can be recovered from our Eq. (12) and Eq. (13) in the limit $\Lambda \rightarrow \infty$, i.e., when no cutoff is made.

The effects of the cutoff are not trivial in the ac case. It is essential to examine those effects in detail as they have a strong bearing on the analysis of the experimental data. The prefactor in Eq. (11) depends only on temperature while the cutoff parameter Λ is found only in the \mathcal{S} functions. Therefore, the effects of the cutoff can be studied through the \mathcal{S} functions alone. We can look at the temperature and frequency dependences of these functions with and without the cutoff. Figure 1(a) shows a set of \mathcal{S}_1 curves as functions of $\xi(T)/\xi_0$ for three different frequencies. Far above T_c the relaxation time τ_0 is so short that $\omega\tau_0 \ll 1$ for any of the chosen frequencies. Therefore the response of the system is

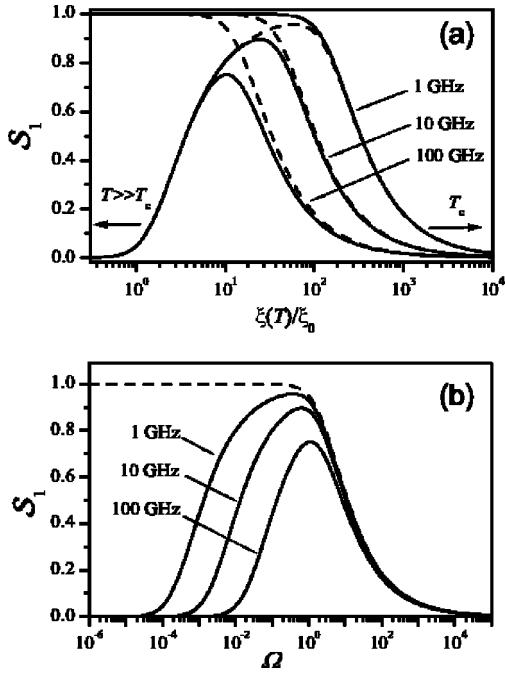


FIG. 1. S_1 curves for the 3D isotropic case calculated from Eq. (12) for a finite cutoff parameter $\Lambda=0.5$ (solid lines) and for $\Lambda=\infty$ (dashed lines). The variable is $\xi(T)/\xi_0$ in (a) and Ω in (b). The curves are labeled by the frequency $\omega/2\pi$ used in the calculations.

like in the dc case. With no cutoff, S_1 saturates to unity [dashed lines in Fig. 1(a)]. This limit is required in order that σ_1 from Eq. (11) becomes equal to $\sigma_{dc}(\Lambda \rightarrow \infty)$ in Eq. (7). If a cutoff with a finite Λ is included, S_1 decays at higher temperatures [solid lines in Fig. 1(a)]. The reduction of S_1 is more pronounced at smaller values of $\xi(T)$ since the integration in q space is terminated at a lower value $Q = \sqrt{3}\Lambda\xi(T)/\xi_0$. At higher temperatures the conductivity σ_1 at any frequency behaves asymptotically as σ_{dc} given by Eq. (8).

At temperatures closer to T_c the relaxation time τ_0 increases as $\xi(T)^2$ with increasing correlation length according to Eq. (3) which is usually termed the critical slowing down. When $\omega\tau_0 \approx 1$ for a given frequency, S_1 is sharply reduced and vanishes in the limit of T_c . With the diverging prefactor in Eq. (11) it can still yield a finite σ_1 at T_c . It may appear from Fig. 1(a) that a cutoff has no effect when T_c is approached, but we show later that an important feature still persists in σ_1 .

Obviously, at lower operating frequencies one needs to approach T_c closer so that the critical slowing down could reach the condition $\omega\tau_0 \approx 1$. One can see from Fig. 1(a) that for frequencies below 1 GHz one would have to approach T_c closer than 1 mK in order to probe the critical slowing down in fluctuations. The higher the frequency, the farther above T_c is the temperature where the crossover $\omega\tau_0 \approx 1$ occurs. This feature expresses the scaling property of the conductivity in frequency and temperature variables. However, the scaling property holds strictly only in the absence of the cutoff. Namely, if one sets $\Lambda \rightarrow \infty$, the function S_1 depends only on the scaling variable Ω . Figure 1(b) shows the same

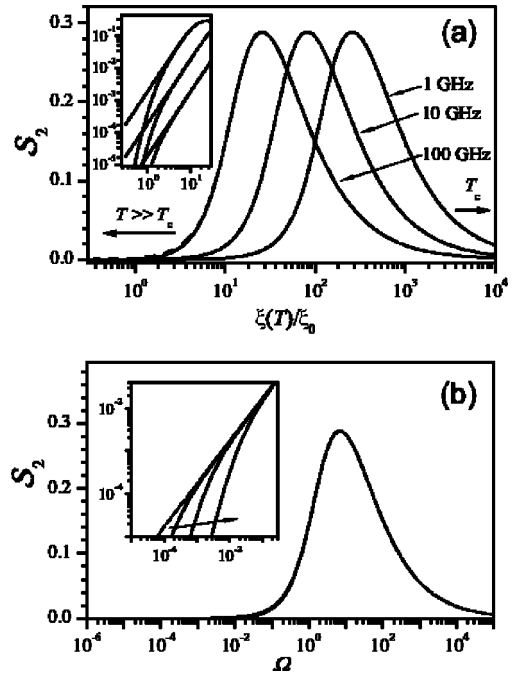


FIG. 2. S_2 curves for the 3D isotropic case calculated from Eq. (13) for the same parameters as in Fig. 1. The effects of a finite cutoff are small and can be seen only on logarithmic scales used in the insets.

set of curves as in Fig. 1(a), but plotted versus Ω . The three dashed curves from Fig. 1(a) coalesce into one dashed curve in Fig. 1(b), thus showing the scaling property in the absence of a cutoff. However, the solid lines representing the functions S_1 with a finite cutoff parameter Λ do not scale with the variable Ω . The reason is that the function S_1 then depends also on Q , which itself is not a function of Ω . Namely, the cutoff in q space depends on the properties of the sample and on the temperature, but not on the frequency used in the experiment. Hence, the cutoff brings about a breakdown of the scaling property in frequency and temperature. The effect is more pronounced at temperatures farther above T_c where the cutoff is stronger.

The properties of the function S_2 are shown in Fig. 2 for the same set of three measurement frequencies as in Fig. 1. When plotted versus $\xi(T)/\xi_0$, the function S_2 exhibits a maximum at the point where the corresponding function S_1 shows the characteristic crossover due to $\omega\tau_0 \approx 1$ as discussed above. When T_c is approached, S_2 tends to zero. When S_2 is multiplied with the diverging prefactor in Eq. (11), one finds a finite σ_2 at T_c . Far above T_c , the function S_2 vanishes, regardless of the cutoff. This is consistent with the behavior of S_1 . Namely, at high enough temperatures, S_1 acquires asymptotically the dc value, as seen in Fig. 1. Obviously, the imaginary part of the conductivity must vanish when the dc-like limit is approached. The decrease of the function S_2 at higher temperatures is very rapid so that the effects of the cutoff are unnoticeable on the linear scale. Only with the logarithmic scale used in the inset to Fig. 2(a) does one observe that the cutoff effects are present also in

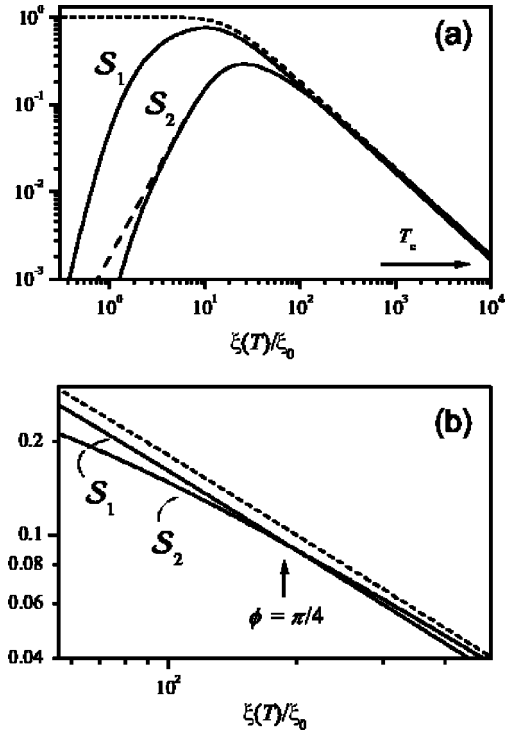


FIG. 3. (a) Asymptotic behavior of the functions S_1 and S_2 of the 3D isotropic case calculated with the choice $\omega/2\pi = 100$ GHz in the limit $T \rightarrow T_c$. The dashed lines are the $S_{1,2}$ curves calculated with no cutoff ($\Lambda = \infty$), and the solid lines include a finite cutoff ($\Lambda = 0.5$). (b) Enlarged section which shows the crossing of S_1 and S_2 ($\phi = \pi/4$; see text) at a temperature slightly above T_c . The two dashed lines are indistinguishable in this temperature range.

S_2 , though by a very small amount. Figure 2(b) shows the scaling property of S_2 with no cutoff and its breakdown when the cutoff is included.

We have noted above that both S_1 and S_2 tend to zero when T_c is approached. Also, the effect of the cutoff is seen to be small in that limit. Yet these functions are multiplied by the diverging prefactor in Eq. (11) and then may yield finite σ_1 and σ_2 . A careful analysis is needed in order to find the phase ϕ of the complex conductivity [$\phi = \arctan(\sigma_2/\sigma_1)$] at T_c . For a 3D isotropic superconductor, Dorsey²² has predicted $\phi = \pi/4$, i.e., $\sigma_1 = \sigma_2$ at T_c . His result was obtained with no cutoff and it remains to be seen if this property is preserved even when a finite cutoff is made. Figure 3(a) shows S_1 and S_2 as functions of $\xi(T)/\xi_0$ for 100 GHz frequency. The effects of cutoff on S_2 are noticeable only far above T_c . Closer to T_c , the curves for S_2 calculated with and without the cutoff are indistinguishable. In contrast, a finite cutoff reduces the values of S_1 even in the limit of T_c . As a result, the final cutoff parameter Λ yields a crossing of the curves for S_1 and S_2 at some temperature slightly above T_c . It is better seen on an enlarged scale in Fig. 3(b). This is a surprising result which has bearing on the experimental observations. Due to the cutoff, the condition $S_1 = S_2$ ($\phi = \pi/4$) is reached at a temperature slightly above T_c . Since both S_1 and S_2 are multiplied with the same prefactor in Eq. (11), one finds that the crossing of $\sigma_1(T)$ and $\sigma_2(T)$ does not occur at the peak of $\sigma_1(T)$, but at a slightly higher tempera-

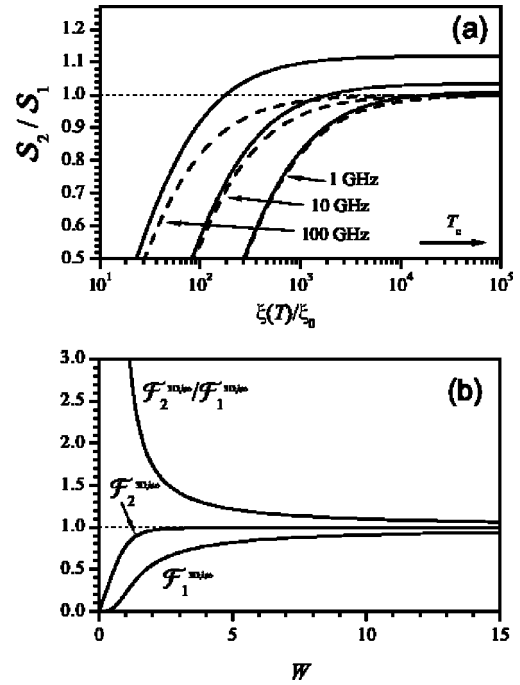


FIG. 4. (a) The ratio S_2/S_1 (equal to σ_2/σ_1) for the 3D isotropic case at temperatures approaching T_c . With no cutoff (dashed lines) the ratio tends to unity for all frequencies. With a finite cutoff ($\Lambda = 0.5$) the ratio equals unity at a temperature slightly above T_c , dependent on the frequency. In the limit $T \rightarrow T_c$ the ratio saturates to a frequency-dependent value larger than unity. (b) The ratio S_2/S_1 and $\mathcal{F}_{1,2}$ given by Eq. (22). The variable W is defined by Eq. (20).

ture. Exactly at T_c , σ_2 is higher than σ_1 since a finite cutoff parameter reduces σ_1 , but has no effect on σ_2 .

The observation that the cutoff brings about a reduction of σ_1 at T_c is worth further investigation since it can be measured experimentally. Figure 4(a) shows the ratio S_2/S_1 (equal to σ_2/σ_1) at temperatures approaching T_c . With no cutoff [dashed lines in Fig. 4(a)], this ratio reaches unity regardless of the frequency used. A finite cutoff parameter [$\Lambda = 0.5$ in Fig. 4(a)] makes the ratio equal to unity at a temperature slightly above T_c , and in the limit of T_c the ratio saturates at some higher value. The saturation level is seen to be higher when a higher frequency is used.

One can find analytical expansions of the S functions in the limit of T_c ($\Omega \rightarrow \infty$). The leading terms are

$$S_{1,2}^{3D,iso}(W, \Omega \rightarrow \infty) \approx \frac{4\sqrt{2}}{3\pi} \left(C \mp \frac{1}{2}D \right) \frac{1}{\sqrt{\Omega}}, \quad (17)$$

where we used the notation

$$C = \arctan(1 + \sqrt{2}W) - \arctan(1 - \sqrt{2}W), \quad (18)$$

$$D = \ln \left(\frac{1 + \sqrt{2}W + W^2}{1 - \sqrt{2}W + W^2} \right). \quad (19)$$

The parameter W depends on the frequency ω and the cutoff parameter Λ :

$$W = \sqrt{3} \Lambda \sqrt{\frac{16 k_B T_c}{\pi \hbar \omega}}. \quad (20)$$

Both functions tend to zero in the limit of T_c ($\Omega \rightarrow \infty$), but their ratio is finite and depends on the parameter W . Figure 4(b) shows the plot of $\mathcal{S}_2/\mathcal{S}_1$ at T_c as a function of W . One can observe that for a given cutoff parameter Λ , the ratio $\mathcal{S}_2/\mathcal{S}_1$ at T_c increases at higher frequencies (lower W). The limits at T_c in Fig. 4(a) represent only three selected points on the curve for $\mathcal{S}_2/\mathcal{S}_1$ in Fig. 4(b).

In a given experiment, the ratio σ_2/σ_1 at T_c can be directly determined from the experimental data so that the corresponding value of the parameter W can be found uniquely from the curve of $\mathcal{S}_2/\mathcal{S}_1$ in Fig. 4(b), and the cutoff parameter Λ is obtained using Eq. (20). We should note that Λ is a temperature-independent parameter. It can be determined by the above procedure from the experimental data at T_c , but it controls the cutoff at all temperatures.

One may observe from Eq. (17) that in the limit of T_c the leading terms in the expansions of the \mathcal{S} functions behave as $(\xi(T)/\xi_0)^{-z/2}$. Taking into account the prefactor in Eq. (11) one finds that σ_1 and σ_2 can have finite nonzero values at T_c only if $z=2$, i.e., for the purely relaxational dynamics. We have assumed this case in all the figures of this section.

From the experimental data at T_c one can determine also the parameter ξ_0 . Using Eq. (11) and the \mathcal{S} functions in Eq. (17), one obtains finite conductivities at T_c :

$$\sigma_{1,2}^{3D,iso}(\omega, T_c, \Lambda) = \frac{e^2}{6\hbar \xi_0} \sqrt{\frac{2 k_B T_c}{\pi \hbar \omega}} \mathcal{F}_{1,2}^{3D,iso}(W), \quad (21)$$

where

$$\sigma_1^{3D,aniso} = \left(\frac{2e\hbar}{m_{ab}\alpha} \right)^2 k_B T_c \sum_{\mathbf{k}} \frac{k_x^2 \tau_0 / 2}{(1 + k_{ab}^2 \xi_{ab}^2 + k_c^2 \xi_c^2) [\Omega^2 + (1 + k_{ab}^2 \xi_{ab}^2 + k_c^2 \xi_c^2)^2]}. \quad (23)$$

Taking $k_x^2 = k_{ab}^2/2$ and substituting the variables $q_{ab} = k_{ab} \xi_{ab}$ and $q_c = k_c \xi_c$, one can evaluate the sum in Eq. (23) by integration in the q_{ab} plane and along the q_c axis:

$$\sigma_1^{3D,aniso}(\omega, T, \Lambda_{ab}, \Lambda_c) = \frac{e^2}{8\pi\hbar \xi_{0c}} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1} \int_0^{Q_{ab}} \int_{-Q_c}^{Q_c} \frac{q_{ab}^3}{(1 + q_{ab}^2 + q_c^2) [\Omega^2 + (1 + q_{ab}^2 + q_c^2)^2]} dq_{ab} dq_c, \quad (24)$$

where we allowed a cutoff $Q_{ab}(T) = \sqrt{2} \Lambda_{ab} \xi_{ab}(T)/\xi_{0ab}$ in the q_{ab} plane and a possibly different cutoff $Q_c(T) = \Lambda_c \xi_c(T)/\xi_{0c}$ along the q_c axis. The dimensionless parameter Ω is the same as given by Eq. (6). We use the notation $\xi(T)/\xi_0$ for both $\xi_{ab}(T)/\xi_{0ab}$ and $\xi_c(T)/\xi_{0c}$.

We may briefly examine the dc case ($\Omega=0$). With no cutoff one obtains

$$\sigma_{dc}^{3D,aniso}(T, \Lambda_{ab,c} \rightarrow \infty) = \frac{e^2}{32\hbar \xi_{0c}} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1}, \quad (25)$$

which reduces to the Aslamazov-Larkin result for $z=2$ (relaxational dynamics) and $\xi(T)/\xi_0$ taken in the Gaussian limit. Note that the fluctuation conductivity in the ab plane depends on ξ_{0c} . Finite cutoff parameters reduce the fluctuation conductivity when the temperature is increased above T_c :

As explained above, from the ratio of the experimental values $\sigma_2(T_c)/\sigma_1(T_c)$ at T_c one can determine the parameter W , and the values of $\mathcal{F}_{1,2}$ can then be calculated from Eq. (22). The remaining unknown parameter ξ_0 can be obtained using Eq. (21) and either of the experimental values of $\sigma_1(T_c)$ or $\sigma_2(T_c)$.

It is also interesting to look at the plots of $\mathcal{F}_{1,2}(W)$ in Fig. 4(b). One can observe that \mathcal{F}_2 saturates to unity already at small values of $W \geq 2$. On the other hand, \mathcal{F}_1 is smaller than unity at any finite value of W , in conformity with the ratio $(\mathcal{F}_2/\mathcal{F}_1) = (\mathcal{S}_2/\mathcal{S}_1)$ at T_c . At this point it is useful to find the expected range of values of W encountered in the experiments. For microwave frequencies in the range 1–100 GHz, with $\Lambda=0.5$, and $T_c=100$ K, one finds that W is in the range 9–90. According to Fig. 4(b), $\mathcal{F}_2 \approx 1$ in this range. This means that the cutoff makes no effect on \mathcal{S}_2 , and only \mathcal{S}_1 is reduced, in conformity with the calculated curves shown in Fig. 3.

III. ANISOTROPY

Most high- T_c superconductors are anisotropic, some of them even having a high value of the anisotropy parameter $\gamma = \xi_{0ab}/\xi_{0c}$. Therefore, for practical purposes one needs adequate expressions for the ac fluctuation conductivity. The real part of the fluctuation conductivity in the ab plane is obtained using the Kubo formalism as in the isotropic case. One obtains

$$\sigma_{dc}^{3D,aniso}(T, \Lambda_{ab}, \Lambda_c) = \frac{e^2}{16\pi\hbar\xi_{0c}} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1} \left[\arctan(Q_c) - \frac{Q_{ab}^2 Q_c}{2(1+Q_{ab}^2)(1+Q_{ab}^2+Q_c^2)} - \frac{2+3Q_{ab}^2}{2(1+Q_{ab}^2)^{3/2}} \arctan\left(\frac{Q_c}{\sqrt{1+Q_{ab}^2}} \right) \right]. \quad (26)$$

This expression has not been reported in the previous literature. Analysis of a dc fluctuation conductivity is difficult because of the number of unknown parameters.

The ac fluctuation conductivity can be obtained from the integral in Eq. (24) for the real part while the imaginary part is obtained by a procedure analogous to that of the isotropic case described in the preceding section:

$$\sigma_2^{3D,aniso}(\omega, T, \Lambda_{ab}, \Lambda_c) = \frac{e^2}{8\pi\hbar\xi_{0c}} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1} \int_0^{Q_{ab}} \int_{-Q_c}^{Q_c} \frac{\Omega q_{ab}^3}{(1+q_{ab}^2+q_c^2)^2 [\Omega^2 + (1+q_{ab}^2+q_c^2)^2]} dq_{ab} dq_c. \quad (27)$$

The full expression can again be written in the form

$$\tilde{\sigma}^{3D,aniso}(\omega, T, \Lambda_{ab}, \Lambda_c) = \frac{e^2}{32\hbar\xi_{0c}} \left(\frac{\xi(T)}{\xi_0} \right)^{z-1} [S_1^{3D,aniso}(\omega, T, \Lambda_{ab}, \Lambda_c) + iS_2^{3D,aniso}(\omega, T, \Lambda_{ab}, \Lambda_c)]. \quad (28)$$

The S functions for the 3D anisotropic case are found to be

$$S_1^{3D,aniso}(\omega, T, \Lambda_{ab}, \Lambda_c) = \frac{1}{3\pi\Omega^2} [2Q_c(3+Q_c^2)L_1 + P_-(P_+^2+2)L_2 - T_-(T_+^2+2-Q_{ab}^2)L_3 + 2P_+(P_-^2-2)A_1 - 2T_+(T_-^2-2+Q_{ab}^2)A_2 - 8\sqrt{1+Q_{ab}^2}(2-Q_{ab}^2)A_3 + 16A_4 + 12\Omega Q_c A_5], \quad (29)$$

$$S_2^{3D,aniso}(\omega, T, \Lambda_{ab}, \Lambda_c) = \frac{1}{3\pi\Omega^2} \left[4Q_c(3+Q_c^2)A_5 + 2P_-(P_+^2+2)A_1 - 2T_-(T_+^2+2-Q_{ab}^2)A_2 - P_+(P_-^2-2)L_2 + T_+(T_-^2-2+Q_{ab}^2)L_3 + 12\Omega \frac{2+Q_{ab}^2}{\sqrt{1+Q_{ab}^2}} A_3 - 24\Omega A_4 - 6\Omega Q_c L_1 \right], \quad (30)$$

where we used the shorthand notations for P_{\pm} as in Eq. (14) and the following:

$$T_{\pm} = \sqrt{2} \sqrt{\sqrt{(1+Q_{ab}^2)^2 + \Omega^2} \pm (1+Q_{ab}^2)}, \quad (31)$$

$$L_1 = \ln \left(\frac{(1+Q_c^2)^2 [\Omega^2 + (1+Q_{ab}^2+Q_c^2)^2]}{(1+Q_{ab}^2+Q_c^2)^2 [\Omega^2 + (1+Q_c^2)^2]} \right), \quad (32)$$

$$L_2 = \ln \left(\frac{2+Q_c^2 + (Q_c - P_-)^2}{2+Q_c^2 + (Q_c + P_-)^2} \right), \quad (33)$$

$$L_3 = \ln \left(\frac{2(1+Q_{ab}^2) + Q_c^2 + (Q_c - T_-)^2}{2(1+Q_{ab}^2) + Q_c^2 + (Q_c + T_-)^2} \right), \quad (34)$$

$$A_1 = \arctan \left(\frac{2Q_c + P_-}{P_+} \right) + \arctan \left(\frac{2Q_c - P_-}{P_+} \right), \quad (35)$$

$$A_2 = \arctan \left(\frac{2Q_c + T_-}{T_+} \right) + \arctan \left(\frac{2Q_c - T_-}{T_+} \right), \quad (36)$$

$$A_3 = \arctan \left(\frac{Q_c}{\sqrt{1+Q_{ab}^2}} \right), \quad (37)$$

$$A_4 = \arctan(Q_c), \quad (38)$$

$$A_5 = \arctan \left(\frac{1+Q_{ab}^2+Q_c^2}{\Omega} \right) - \arctan \left(\frac{1+Q_c^2}{\Omega} \right). \quad (39)$$

The effects of the cutoff are similar as those described at length in the preceding section for the simpler case of 3D isotropic superconductors. In this section we discuss only the modifications in the limit $T \rightarrow T_c$ where the relevant parameters can be determined. The S functions can be expanded in the limit of T_c ($\Omega \rightarrow \infty$), and the leading terms are

$$\begin{aligned}
& \mathcal{S}_1^{3D,aniso}(W_{ab}, W_c, \Omega \rightarrow \infty) \\
& \approx \frac{4\sqrt{2}}{3\pi} \left[C_1 - U_+ \left(\sqrt{1+W_{ab}^4} - \frac{1}{2} W_{ab}^2 \right) C_2 \right. \\
& \quad + \frac{3}{\sqrt{2}} W_c C_3 + \sqrt{2} W_{ab}^3 C_4 - \frac{1}{2} D_1 + \frac{1}{2} U_- \left(\sqrt{1+W_{ab}^4} \right. \\
& \quad \left. \left. + \frac{1}{2} W_{ab}^2 \right) D_2 + \frac{1}{2\sqrt{2}} W_c^3 D_3 \right] \frac{1}{\sqrt{\Omega}}, \quad (40)
\end{aligned}$$

$$\begin{aligned}
& \mathcal{S}_2^{3D,aniso}(W_{ab}, W_c, \Omega \rightarrow \infty) \\
& \approx \frac{4\sqrt{2}}{3\pi} \left[C_1 - U_- \left(\sqrt{1+W_{ab}^4} + \frac{1}{2} W_{ab}^2 \right) C_2 \right. \\
& \quad + \frac{1}{\sqrt{2}} W_c^3 C_3 + \frac{3}{\sqrt{2}} W_{ab} C_4 + \frac{1}{2} D_1 \\
& \quad \left. - \frac{1}{2} U_+ \left(\sqrt{1+W_{ab}^4} - \frac{1}{2} W_{ab}^2 \right) D_2 - \frac{3}{2\sqrt{2}} W_c D_3 \right] \frac{1}{\sqrt{\Omega}}, \quad (41)
\end{aligned}$$

where we used the following shorthand notation:

$$U_{\pm} = \sqrt{\sqrt{1+W_{ab}^4} \pm W_{ab}^2}, \quad (42)$$

$$C_1 = \arctan(1 + \sqrt{2} W_c) - \arctan(1 - \sqrt{2} W_c), \quad (43)$$

$$C_2 = \arctan\left(\frac{U_- + \sqrt{2} W_c}{U_+}\right) - \arctan\left(\frac{U_- - \sqrt{2} W_c}{U_+}\right), \quad (44)$$

$$C_3 = \arctan(W_{ab}^2 + W_c^2) - \arctan(W_c^2), \quad (45)$$

$$C_4 = \arctan\left(\frac{W_c}{W_{ab}}\right), \quad (46)$$

$$D_1 = \ln\left(\frac{1 + \sqrt{2} W_c + W_c^2}{1 - \sqrt{2} W_c + W_c^2}\right), \quad (47)$$

$$D_2 = \ln\left(\frac{\sqrt{1+W_{ab}^4} + \sqrt{2} W_c U_- + W_c^2}{\sqrt{1+W_{ab}^4} - \sqrt{2} W_c U_- + W_c^2}\right), \quad (48)$$

$$D_3 = \ln\left(\frac{W_c^4 [1 + (W_{ab}^2 + W_c^2)^2]}{(W_{ab}^2 + W_c^2)^2 (1 + W_c^4)}\right). \quad (49)$$

The cutoff parameters appear in

$$W_{ab} = \sqrt{2} \Lambda_{ab} \sqrt{\frac{16 k_B T_c}{\pi \hbar \omega}}, \quad (50)$$

$$W_c = \Lambda_c \sqrt{\frac{16 k_B T_c}{\pi \hbar \omega}}. \quad (51)$$

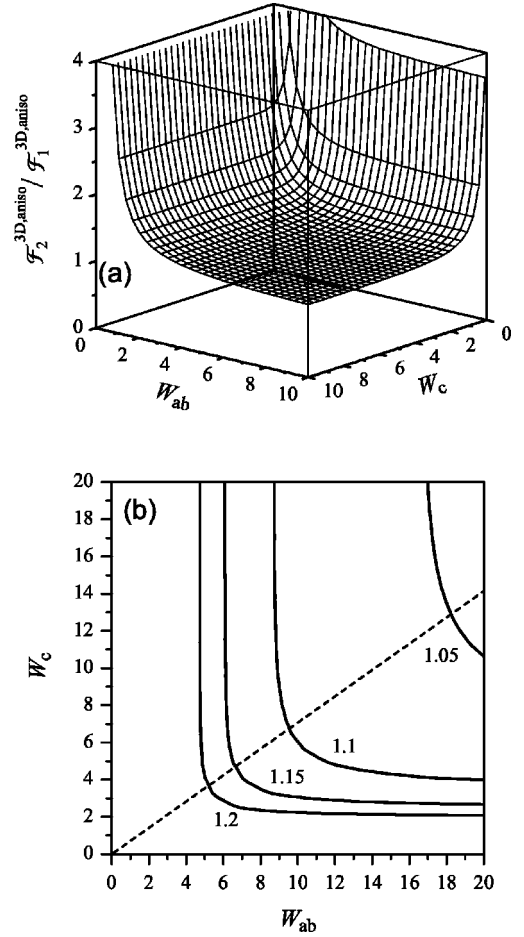


FIG. 5. (a) The ratio $\mathcal{F}_2/\mathcal{F}_1$ for 3D anisotropic case as a function of W_{ab} and W_c [cf. Eq. (52)]. (b) Selection of curves for fixed ratios of $\mathcal{F}_2/\mathcal{F}_1$ indicated by numbers. The dashed line marks the condition $\Lambda_{ab} = \Lambda_c$ ($W_{ab} = \sqrt{2} W_c$).

We note that in the anisotropic case, the \mathcal{S} functions behave also as $1/\sqrt{\Omega}$ when $T \rightarrow T_c$. As already discussed in the previous section, this implies that finite nonzero $\sigma_1(T_c)$ and $\sigma_2(T_c)$ can be obtained only for $z=2$ (relaxational model). Since the available experimental data in anisotropic high- T_c superconductors⁶⁻⁸ show finite nonzero $\sigma_1(T_c)$ and $\sigma_2(T_c)$, we can adopt $z=2$ in the remainder of this section.

In analogy to the 3D isotropic case described in the preceding section, one may define the functions

$$\mathcal{F}_{1,2}^{3D,aniso}(W_{ab}, W_c) = \frac{3\sqrt{\Omega}}{4\sqrt{2}} \mathcal{S}_{1,2}^{3D,aniso}(W_{ab}, W_c, \Omega \rightarrow \infty), \quad (52)$$

so that the conductivities at T_c are given by

$$\begin{aligned}
\sigma_{1,2}^{3D,aniso}(\omega, T_c, \Lambda_{ab}, \Lambda_c) &= \frac{e^2}{6\hbar \xi_{0c}} \sqrt{\frac{2 k_B T_c}{\pi \hbar \omega}} \\
&\quad \times \mathcal{F}_{1,2}^{3D,aniso}(W_{ab}, W_c). \quad (53)
\end{aligned}$$

The ratio of experimental values σ_2/σ_1 at T_c does not define uniquely the cutoff parameters Λ_{ab} and Λ_c . It puts, however, a constraint on their choice. Figure 5(a) shows the plot

of $\mathcal{F}_2/\mathcal{F}_1$ given by Eq. (52) as a function of two variables W_{ab} and W_c . It is evident that a fixed value of $\mathcal{F}_2/\mathcal{F}_1$ defines a simple curve of possible choices of (W_{ab}, W_c) . Figure 5(b) shows a selection of such curves for $\mathcal{F}_2/\mathcal{F}_1 = 1.05, 1.1, 1.15, \text{ and } 1.2$. The dashed line marks the condition $\Lambda_{ab} = \Lambda_c$ ($W_{ab} = \sqrt{2}W_c$). Experimentally, one has to probe the possible choices for (W_{ab}, W_c) and look at the fits of the theoretical curves to the experimental data at $T > T_c$. The parameter ξ_{0c} in Eq. (28) can be obtained once the choice for (W_{ab}, W_c) is made.

Note that in practical applications of the above theory one needs measurements where the microwave current flows only in the ab plane. Particularly suitable for this purpose are the measurements in which the superconducting sample is placed in the antinode of the microwave electric field E_ω in the cavity.^{34,35}

IV. TWO-DIMENSIONAL FLUCTUATIONS

The superconducting transition does not occur in a strictly 2D system. However, if the sample is a very thin film so that its thickness is much smaller than the correlation length, the fluctuations will be restricted within the film thickness d in one direction and develop freely only in the plane of the film. Using the formalism described in the preceding sections, we find that the fluctuation conductivity is given by

$$\begin{aligned} \sigma_1^{2D}(\omega, T, \Lambda) &= \frac{e^2}{4\hbar d} \left(\frac{\xi(T)}{\xi_0} \right)^2 \\ &\times \sum_{q_n} \int_0^Q \frac{q^3}{(1+q^2+q_n^2)[\Omega^2+(1+q^2+q_n^2)^2]} dq, \end{aligned} \quad (54)$$

$$\begin{aligned} \sigma_2^{2D}(\omega, T, \Lambda) &= \frac{e^2}{4\hbar d} \left(\frac{\xi(T)}{\xi_0} \right)^2 \\ &\times \sum_{q_n} \int_0^Q \frac{\Omega q^3}{(1+q^2+q_n^2)^2[\Omega^2+(1+q^2+q_n^2)^2]} dq, \end{aligned} \quad (55)$$

$$\begin{aligned} \bar{\sigma}^{2D}(\omega, T, \Lambda) &= \frac{e^2}{16\hbar d} \left(\frac{\xi(T)}{\xi_0} \right)^2 \sum_{q_n} [\mathcal{S}_1^{2D}(\Omega, Q, q_n) \\ &+ i\mathcal{S}_2^{2D}(\Omega, Q, q_n)], \end{aligned} \quad (56)$$

where

$$q_n = n\pi \left(\frac{\xi_0}{d} \right) \left(\frac{\xi(T)}{\xi_0} \right) \quad (57)$$

and $Q = \sqrt{2}\Lambda(\xi(T)/\xi_0)$. The prefactor is the Aslamazov-Larkin result for the 2D case with no cutoff and the Gaussian form $1/\epsilon$ replaced by the more general expression $(\xi(T)/\xi_0)^2$.

The \mathcal{S} functions are given by

$$\begin{aligned} \mathcal{S}_1^{2D}(\Omega, Q, q_n) &= \frac{1}{\Omega} \left[2 \arctan \left(\frac{1+Q^2+q_n^2}{\Omega} \right) \right. \\ &- 2 \arctan \left(\frac{1+q_n^2}{\Omega} \right) + \left. \left(\frac{1+q_n^2}{\Omega} \right) \right. \\ &\times \left. \ln \left(\frac{(1+q_n^2)^2[\Omega^2+(1+Q^2+q_n^2)^2]}{(1+Q^2+q_n^2)^2[\Omega^2+(1+q_n^2)^2]} \right) \right], \end{aligned} \quad (58)$$

$$\begin{aligned} \mathcal{S}_2^{2D}(\Omega, Q, q_n) &= \frac{1}{\Omega} \left[\frac{2(1+q_n^2)}{\Omega} \left[\arctan \left(\frac{1+Q^2+q_n^2}{\Omega} \right) \right. \right. \\ &- \left. \left. \arctan \left(\frac{1+q_n^2}{\Omega} \right) \right] \right. \\ &- \left. \ln \left(\frac{(1+q_n^2)^2[\Omega^2+(1+Q^2+q_n^2)^2]}{(1+Q^2+q_n^2)^2[\Omega^2+(1+q_n^2)^2]} \right) \right. \\ &- \left. 2 \frac{Q^2}{1+Q^2+q_n^2} \right]. \end{aligned} \quad (59)$$

The summation over q_n in Eq. (56) has to be carried out until the factor $n\pi(\xi_0/d)$ reaches some cutoff value Λ , which is of the order of unity. If the film thickness is large ($d \gg \xi_0$), one has to sum up to a high n value. In such cases, the summation is well approximated by an integration, and one retrieves the 3D case of the preceding section. The 2D character is better displayed when the film thickness is comparable to ξ_0 . Then, only a few terms have to be taken into account. In the extreme case of $d < \xi_0$, only the $n=0$ term is found below the cutoff limit.

The zero-frequency limit ($\Omega \rightarrow 0$) yields

$$\sigma_{dc}^{2D}(T, \Lambda) = \frac{e^2}{16\hbar d} \left(\frac{\xi(T)}{\xi_0} \right)^2 \sum_{q_n} \frac{Q^4}{(1+Q^2+q_n^2)^2(1+q_n^2)}. \quad (60)$$

The $n=0$ term yields the previous result of Hopfengärtner *et al.*⁴ and Gauzzi *et al.*⁵

In the limit of T_c ($\Omega \rightarrow \infty$) one obtains

$$\begin{aligned} \sigma_1^{2D}(T_c) &= \frac{e^2}{\pi\hbar d} \frac{k_B T_c}{\hbar\omega} \sum_n \left[2 \arctan(W^2 + W_n^2) \right. \\ &- \left. 2 \arctan(W_n^2) + W_n^2 \ln \frac{W_n^4[1+(W^2+W_n^2)^2]}{(1+W_n^4)(W^2+W_n^2)^2} \right], \end{aligned} \quad (61)$$

$$\sigma_2^{2D}(T_c) = \frac{e^2}{\pi \hbar d} \frac{k_B T_c}{\hbar \omega} \sum_n \left[2W_n^2 \arctan(W^2 + W_n^2) - 2W_n^2 \arctan(W_n^2) - \ln \frac{W_n^4 [1 + (W^2 + W_n^2)^2]}{(1 + W_n^4)(W^2 + W_n^2)^2} \right], \quad (62)$$

where we used the notation

$$W = \sqrt{2} \Lambda \sqrt{\frac{16 k_B T_c}{\pi \hbar \omega}}, \quad (63)$$

$$W_n = n \pi \left(\frac{\xi_0}{d} \right) \sqrt{\frac{16 k_B T_c}{\pi \hbar \omega}}. \quad (64)$$

One may observe that for $n=0$ the real part of the conductivity is finite, but the imaginary part diverges. It is due to the logarithmic term in Eq. (62). This is an unphysical result. It may indicate that the $n=0$ term is not physically acceptable or that the 2D model should not be applied exactly at T_c .

V. COMPARISON WITH EXPERIMENT

The relevance of the theoretical expressions derived in the preceding sections can be demonstrated by comparison of the calculated and experimentally measured ac fluctuation conductivity. As an example we present here an analysis of the data in $\text{Bi}_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_{10-\delta}$ (BSCCO) thin film. The experimental results of the complex conductivity measured at 9.5 GHz are shown in Fig. 6(a). The main features are the same as reported previously in single crystals of high- T_c superconductors.^{6,18} We have to note that in our measurement the thin film was positioned in the center of an elliptical microwave cavity resonating in ${}_{e}\text{TE}_{111}$ mode and oriented in such a way that the electric field E_ω was in the ab plane. Thus the in-plane conductivity was measured and the application of the theoretical expressions of the preceding sections is appropriate. The normal-state conductivity $\sigma_n(T)$ was determined from the linear resistivity $\rho_n(T)$ above 160 K. Other experimental details have been reported previously.³⁵⁻³⁷ In this section, we are interested in the fluctuation conductivity near T_c which is shown on an enlarged scale in Fig. 6(b). The real part of the conductivity has a maximum when the coherence length diverges. Since the critical temperature of a phase transition is characterized by the divergence of the coherence length, we use the maximum of σ_1 in Fig. 6(b) to determine $T_c = 84.04$ K. One can also observe in Fig. 6(b) that the imaginary part of the conductivity crosses the real part at a temperature slightly above T_c . This is a consistency test of the short-wavelength cutoff as discussed in Sec. II. The experimental values of σ_1 and σ_2 at T_c can be used in the evaluation of the parameters which enter the theoretical expressions of the preceding sections.

Figure 7(a) shows the experimental data above T_c plotted against the reduced temperature $\epsilon = \ln(T/T_c)$. We can analyze this data first by the theoretical expressions which have no cutoff on the fluctuation wave vector. It is straightforward to evaluate ξ_{0c} using Eq. (53) and the experimental value of σ_2

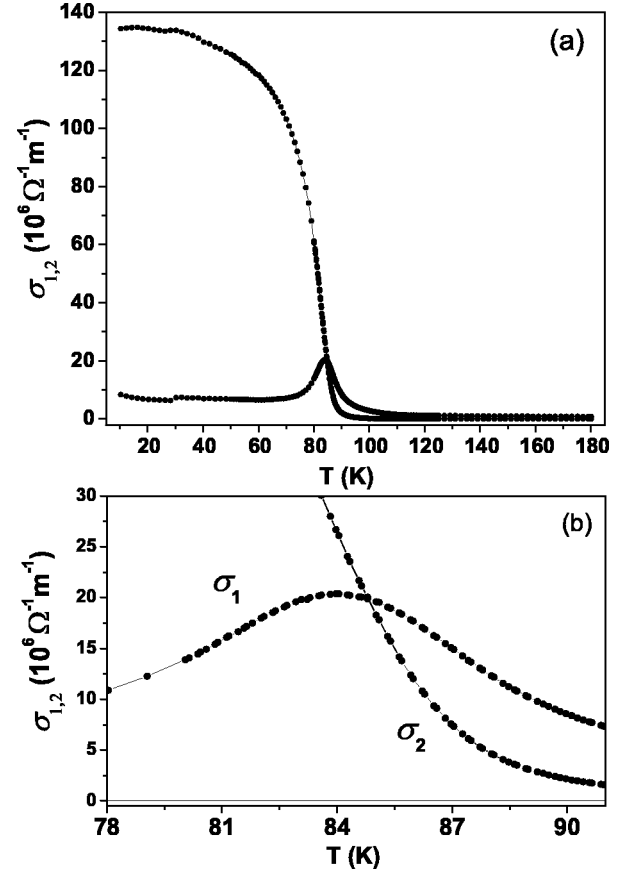


FIG. 6. (a) Experimental complex conductivity in $\text{Bi}_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_{10-\delta}$ thin film at 9.5 GHz. (b) Enlarged section near T_c .

at T_c . The determination of ξ_{0c} from $\sigma_2(T_c)$ does not depend on the choice of the cutoff parameters so that its value can be used in the subsequent data analysis. We have obtained $\xi_{0c} = 0.016$ nm in $\text{Bi}_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_{10-\delta}$ thin film. Once this parameter is determined, the fluctuation conductivity at all temperatures above T_c follows from Eq. (28). The real and imaginary parts of the ac fluctuation conductivity have to be mutually consistent. This can be exploited in the data analysis. We insert the experimental values of σ_2 into the imaginary part of Eq. (28) and solve numerically for $\xi(T)/\xi_0$. Then we exploit these same values of the reduced correlation length in the real part of Eq. (28). The calculated σ_1 is shown by the dotted line in Fig. 7(a). The calculated line lies far from the experimental points. Note in particular that the calculated σ_1 meets σ_2 at T_c when no cutoff is included (cf. Sec. II). Besides, the shape of the calculated σ_1 differs from that of the experimental one. We may conclude that with no cutoff on the fluctuation wave vector the theoretical expression does not describe properly the experimental fluctuation conductivity.

A finite cutoff on the fluctuation wave vector improves greatly the agreement of the theory and experiment. From Fig. 6(b) we can evaluate the ratio $\sigma_2(T_c)/\sigma_1(T_c) = 1.28$ at T_c . This value yields a constraint on the choices of Λ_{ab} and Λ_c as described in Sec. III and Fig. 5. The actual choices are presented in the inset of Fig. 7(b). For a given choice (Λ_{ab} ,

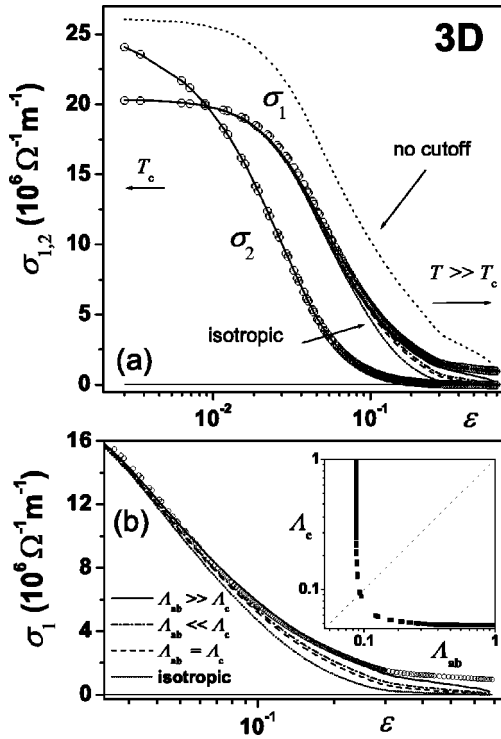


FIG. 7. (a) Experimental data (symbols) of the complex conductivity from Fig. 6 above T_c plotted vs the reduced temperature $\epsilon = (\ln T/T_c)$. Various lines are the conductivities calculated in the 3D cases as described in the text. (b) Enlarged view of the high-temperature part of the same curves as in (a). The constraining curve for the choices of the cutoff parameters Λ_{ab} and Λ_c resulting from the experimental ratio $\sigma_2(T_c)/\sigma_1(T_c) = 1.28$ at T_c is shown in the inset.

Λ_c) from this constraining line, one has to determine first ξ_{0c} using Eq. (53) and the experimental value of σ_2 at T_c . Then, the temperature dependence of the reduced correlation length $\xi(T)/\xi_0$ is evaluated numerically from the imaginary part of Eq. (28) with the selected pair $(\Lambda_{ab}, \Lambda_c)$ and the experimental values of σ_2 . The obtained values of $\xi(T)/\xi_0$ are finally used to calculate σ_1 from the real part of Eq. (28). The results vary with the possible choices of the pairs $(\Lambda_{ab}, \Lambda_c)$ from inset of Fig. 7(b). The best fit of the calculated σ_1 to the experimental points is shown by the solid line in Fig. 7(a). It is obtained with the choice $(\Lambda_{ab} = 0.71, \Lambda_c = 0.05)$. It is physically reasonable. With Λ_{ab} being of the order of unity, the minimum wavelength of the superconducting fluctuations in the ab plane is given by $2\pi\xi_{0ab}$, which is much larger than the atomic size and could be accepted as a mesoscopic quantity. In contrast, the value of $2\pi\xi_{0c}$ is below the atomic size and, hence, could not be physically accepted for the lower limit of the fluctuation wavelength along the c axis. Therefore one needs a value of $\Lambda_c \ll 1$ so that the minimum wavelength of the superconducting fluctuations $2\pi\xi_{0c}/\Lambda_c$ along the c axis becomes also an acceptable mesoscopic quantity.

We have tested also a number of other choices of the cutoff parameters. By shifting the choice of the parameters along the constraining curve in the inset of Fig. 7(b), one

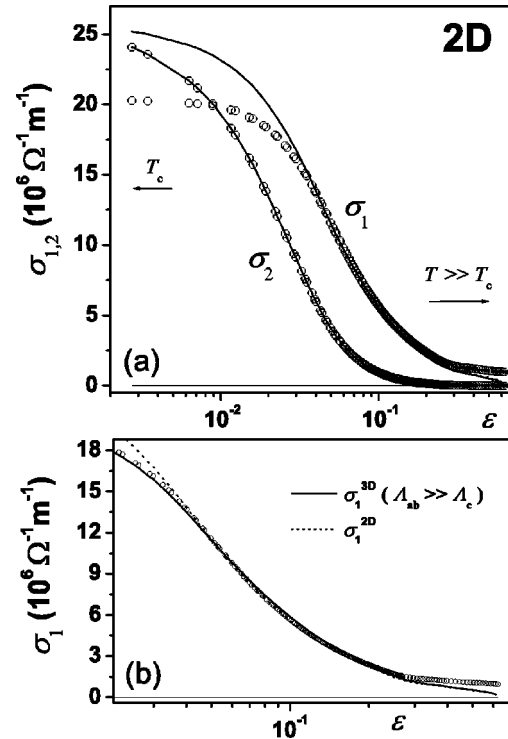


FIG. 8. (a) Experimental data (symbols) as in Fig. 7(a) with the calculated 2D curve as described in the text. (b) The superposition of the calculated 2D and 3D curves.

degrades the fit of the calculated σ_1 to the experimental points. The dashed line in Fig. 7(a) is the calculated σ_1 using the choice of equal cutoff parameters ($\Lambda_{ab} = \Lambda_c = 0.09$) permitted by the constraint in the inset of Fig. 7(b). The fit to the experimental points is seen to be much worse than that of the solid line. For the sake of completeness, we show also the result for a choice of cutoff parameters on the other branch of the constraining curve in the inset of Fig. 7(b). If one takes $\Lambda_{ab} = 0.08, \Lambda_c = 0.71$, the calculated σ_1 is as shown by the dash-dotted line in Fig. 7(a). The fit is unsatisfactory. Moreover, this choice has to be refuted on the grounds of a physically unacceptable minimum wavelength of the fluctuations along the c axis. Also shown in Fig. 7(a) by the short-dotted line is the result obtained by the isotropic 3D expression in Eq. (11). In this case the parameters $\xi_0 = 0.016$ nm and $\Lambda = 0.08$ are obtained straightforwardly from Eq. (21) and the experimental values of σ_1 and σ_2 at T_c . The fit in Fig. 7(a) is obviously not good. It is also seen that the expressions for the anisotropic 3D case always yield curves which are different from that of the isotropic 3D case. The complexity of the anisotropic 3D expressions elaborated in Sec. III is not futile. Indeed, we find that these expressions must be used when analyzing an anisotropic superconductor. Figure 7(b) shows an enlarged view of the high-temperature part where the same curves as in Fig. 7(a) are better distinguished.

We have analyzed also the 2D expressions of Sec. IV. Figure 8(a) shows again the same experimental data as in Fig. 7(a), but fitted with $n=0$ term of the 2D expansion in Eq. (56). The parameter d has been chosen so as to optimize

the fit to the experimental values of σ_1 . The resulting curve in Fig. 8(a) was obtained with $d=1.2$ nm. The 2D results are not so sensitive to the fluctuation wave vector cutoff as those of the 3D case. The curves obtained with no cutoff ($\Lambda = \infty$) and with $\Lambda=0.7$ are practically indistinguishable in Fig. 8(a). One may conclude that closer to T_c the BSCCO superconductor clearly does not behave as a 2D system. However, at higher temperatures both 2D and 3D expressions yield almost equally good fits to the experimental values, as seen in Fig. 8(b). Thus the dimensionality of the fluctuations at higher temperatures cannot be resolved from the ac fluctuation conductivity.

Finally, we remark that the above analysis could explain very well the experimental ac fluctuation conductivity above T_c in the BSCCO thin film using Aslamazov-Larkin-type expressions with wave vector cutoff as deduced in the preceding sections of this paper. The other contributions such as Maki-Thomson and one electron density of states, mentioned in Sec. II, are not necessary over most of the temperature range covered in the experiment. This is in accordance with the recent microscopic calculation³⁸ proving that these contributions may cancel in the ultraclean case of nonlocal electrodynamics. However, they may play a role at high enough temperatures where the above-calculated curves depart from the experimental data. Their analysis is beyond the scope of the present paper.

VI. CONCLUSIONS

We have presented full analytical expressions for the ac fluctuation conductivity in 3D isotropic, 3D anisotropic, and 2D superconductors. The effects of the short-wavelength cutoff in the fluctuation spectrum on the dc and ac conductivities were discussed in detail. The short-wavelength cutoff brings about a breakdown of the scaling property in fre-

quency and temperature. It also has a small, but experimentally very important effect on σ_1 . Due to a finite cutoff parameter Λ , the value of σ_1 at T_c is lower than that of σ_2 . In the simpler 3D isotropic case, this observation can be used to determine Λ directly from the experimental data at T_c . In the 3D anisotropic case, one obtains a constraint on the choices of $(\Lambda_{ab}, \Lambda_c)$.

A useful feature of ac fluctuation conductivity measurements is that T_c can be determined directly from the experimental data. Moreover, the expressions derived in this paper enable the determination of ξ_0 (3D isotropic) or ξ_{0c} (3D anisotropic) from the experimental values $\sigma_{1,2}(T_c)$. Thus, we establish that the analysis of ac fluctuation conductivity requires no free fit parameters in the 3D isotropic case and only one $(\Lambda_{ab}, \Lambda_c)$ in the 3D anisotropic case.

We have shown that the anisotropic 3D expressions with an appropriate cutoff of the fluctuation wave vector can account for the experimental fluctuation conductivity in a BSCCO thin film within a large temperature range above T_c . The 2D expression is less sensitive to the cutoff and was found to match the experimental data only at higher temperatures.

Note added. After the present paper was submitted for publication, several papers dealing with the theory and experiments on the ac fluctuation conductivity with a short-wavelength cutoff were submitted and appeared in the literature.^{39,40}

ACKNOWLEDGMENTS

D.-N.P. and M.M. acknowledge support by the Deutsche Forschungsgemeinschaft (DFG) Project No. Me362/14-2. A.D. acknowledges support from the Croatian Ministry of Science and DLR Stiftung (Project No. KRO-004-98).

*Present address: Philips Research Laboratories, Weisshausstrasse 2, D-52066, Aachen, Germany. Electronic address: dragos.peligrad@philips.com

†Electronic address: m.mehring@physik.uni-stuttgart.de

‡Electronic address: adulcic@phy.hr

¹C. J. Lobb, Phys. Rev. B **36**, 3930 (1987).

²W. J. Skocpol and M. Tinkham, Rep. Prog. Phys. **38**, 1049 (1975).

³M. Ausloos and Ch. Laurent, Phys. Rev. B **37**, 611 (1988).

⁴R. Hopfengärtner, B. Hensel, and G. Saemann-Ischenko, Phys. Rev. B **44**, 741 (1991).

⁵A. Gauzzi and D. Pavuna, Phys. Rev. B **51**, 15 420 (1995).

⁶S. M. Anlage, J. Mao, J. C. Booth, D. H. Wu, and J. L. Peng, Phys. Rev. B **53**, 2792 (1996).

⁷J. C. Booth, D. H. Wu, S. B. Qadri, E. F. Skelton, M. S. Osofsky, A. Piqué, and S. M. Anlage, Phys. Rev. Lett. **77**, 4438 (1996).

⁸J. Kötzler and M. Kaufmann, Phys. Rev. B **56**, 13 734 (1997).

⁹M. R. Cimberle, C. Ferdeghini, E. Giannini, D. Marré, M. Putti, A. Siri, F. Federici, and A. Varlamov, Phys. Rev. B **55**, R14 745 (1997).

¹⁰R. M. Costa, P. Pureur, L. Ghivelder, J. A. Campá, and I. Rasines, Phys. Rev. B **56**, 10 836 (1997).

¹¹S. H. Han, Yu. Eltsev, and Ö. Rapp, Phys. Rev. B **57**, 7510 (1998).

¹²S. H. Han, Yu. Eltsev, and Ö. Rapp, Phys. Rev. B **61**, 11 776 (2000).

¹³E. Silva, S. Sarti, R. Fastampa, and M. Giura, Phys. Rev. B **64**, 144508 (2001).

¹⁴R. M. Costa, P. Pureur, M. Gusmão, S. Senoussi, and K. Behnia, Phys. Rev. B **64**, 214513 (2001).

¹⁵L. Reggiani, R. Vaglio, and A. A. Varlamov, Phys. Rev. B **44**, 9541 (1991).

¹⁶G. Nakielski, D. Görlitz, Chr. Stodte, M. Welters, A. Krämer, and J. Kötzler, Phys. Rev. B **55**, 6077 (1997).

¹⁷D. Neri, E. Silva, S. Sarti, R. Marcon, M. Giura, R. Fastampa, and N. Saprivieri, Phys. Rev. B **58**, 14 581 (1998).

¹⁸J. R. Waldram, D. M. Broun, D. C. Morgan, R. Ormeno, and A. Porch, Phys. Rev. B **59**, 1528 (1999).

¹⁹O. Klein, E. J. Nicol, K. Holczer, and G. Grüner, Phys. Rev. B **50**, 6307 (1994).

²⁰H. Schmidt, Z. Phys. **216**, 336 (1968).

²¹D. S. Fisher, M. P. A. Fisher, and D. A. Huse, Phys. Rev. B **43**, 130 (1991).

²²A. T. Dorsey, Phys. Rev. B **43**, 7575 (1991).

- ²³R. A. Wickham and A. T. Dorsey, Phys. Rev. B **61**, 6945 (2000).
- ²⁴B. R. Patton, V. Ambegaokar, and J. W. Wilkins, Solid State Commun. **7**, 1287 (1969).
- ²⁵J. P. Gollub, M. R. Beasley, R. Callarotti, and M. Tinkham, Phys. Rev. B **7**, 3039 (1973).
- ²⁶W. L. Johnson, C. C. Tsuei, and P. Chaudhari, Phys. Rev. B **17**, 2884 (1978).
- ²⁷M. Tinkham, *Introduction to Superconductivity*, 2nd ed. (McGraw-Hill, New York, 1995).
- ²⁸D. Neri, R. Marcon, E. Silva, R. Fastampa, L. Iacobucci, and S. Sarti, Int. J. Mod. Phys. B **13**, 1097 (1999).
- ²⁹D. Neri, R. Fastampa, M. Giura, R. Marcon, S. Sarti, and E. Silva, J. Low Temp. Phys. **117**, 1099 (1999).
- ³⁰L. G. Aslamazov and A. A. Varlamov, J. Low Temp. Phys. **38**, 223 (1980).
- ³¹F. Federici and A. A. Varlamov, Phys. Rev. B **55**, 6070 (1997).
- ³²A. I. Larkin and A. A. Varlamov, in *Handbook on Superconductivity: Conventional and Unconventional Superconductors*, edited by K.-H. Bennemann and J. B. Ketterson (Springer, Berlin, 2002).
- ³³A. A. Varlamov, G. Balestrino, E. Milani, and D. V. Livanov, Adv. Phys. **48**, 655 (1999).
- ³⁴D.-N. Peligrad, B. Nebendahl, C. Kessler, M. Mehring, A. Dulčić, M. Požek, and D. Paar, Phys. Rev. B **58**, 11 652 (1998).
- ³⁵D.-N. Peligrad, B. Nebendahl, M. Mehring, A. Dulčić, M. Požek, and D. Paar, Phys. Rev. B **64**, 224504 (2001).
- ³⁶B. Nebendahl *et al.*, Rev. Sci. Instrum. **72**, 1876 (2001).
- ³⁷D.-N. Peligrad, B. Nebendahl, M. Mehring, and A. Dulčić, cond-mat/0209176 (unpublished).
- ³⁸D. V. Livanov, G. Savona, and A. A. Varlamov, Phys. Rev. B **62**, 8675 (2000).
- ³⁹E. Silva, Eur. Phys. J. B **27**, 497 (2002).
- ⁴⁰E. Silva *et al.*, cond-mat/0208342 (unpublished); cond-mat/0208343 (unpublished).